

1 **Title:** Microfluidics based manufacture of liposomes simultaneously entrapping hydrophilic
2 and lipophilic drugs.

3 **Authors:** Sameer Joshi¹, Maryam T Hussain², Carla B Roces², Giulia Anderluzzi³, Elisabeth
4 Kastner¹, Stefano Salmaso³, Daniel J Kirby¹, Yvonne Perrie².

5 ¹Aston Pharmacy School, Life and Health Sciences, Aston University, Birmingham, UK. B4 7ET.

6 ²Strathclyde Institute of Pharmacy and Biomedical Sciences, University of Strathclyde, 161
7 Cathedral Street, Glasgow, UK. G4 0RE

8 ³Department of Pharmaceutical and Pharmacological Sciences, University of Padova, Via
9 Marzolo 5, 35131 Padova - Italy.

10

11

12

13

14

15 *Correspondence:
16 Prof Yvonne Perrie
17 Chair in Drug Delivery
18 Strathclyde Institute of Pharmacy & Biomedical Sciences
19 University of Strathclyde
20 161 Cathedral Street
21 Glasgow G4 0RE
22 E-mail: yvonne.perrie@strath.ac.uk

23 **Keywords:** Liposomes, microfluidics, water soluble drugs, poorly soluble drugs, bilayer
24 loading, manufacturing.

25 **Abstract**

26 Despite the substantial body of research investigating the use of liposomes, niosomes and
27 other bilayer vesicles for drug delivery, the translation of these systems into licensed products
28 remains limited. Indeed, recent shortages in the supply of liposomal products demonstrate
29 the need for new scalable production methods for liposomes. Therefore, the aim of our
30 research has been to consider the application of microfluidics in the manufacture of
31 liposomes containing either or both a water soluble and a lipid soluble drug to promote co-
32 delivery of drugs. For the first time, we demonstrate the entrapment of a hydrophilic and a
33 lipophilic drug (metformin and glipizide respectively) both individually and in combination
34 using a scalable microfluidics manufacturing system. In terms of the operating parameters,
35 the choice of solvents, lipid concentration and aqueous:solvent ratio all impact on liposome
36 size with vesicle diameter ranging from ~90 to 300 nm. In terms of drug loading, microfluidics
37 production promoted high loading within ~100 nm vesicles for both the water soluble drug
38 (20 - 25% of initial amount added) and the bilayer embedded drug (40 – 42% of initial amount
39 added) with co-loading of the drugs making no impact on entrapment efficacy. However, co-
40 loading of glipizide and metformin within the same liposome formulation did impact on the
41 drug release profiles; in both instances the presence of both drugs in the one formulation
42 promoted faster (up to 2 fold) release compared to liposomes containing a single drug alone.
43 Overall, these results demonstrate the application of microfluidics to prepare liposomal
44 systems incorporating either or both an aqueous soluble drug and a bilayer loaded drug.

45 **1. Introduction**

46 Since their discovery in the 1960s (Bangham and Horne, 1964) and first application as drug
47 delivery systems (Gregoriadis and Ryman, 1971), liposomes continue to offer new
48 opportunities to improve the delivery and targeting of a range of therapeutic agents, from
49 small molecules through to large biologicals. Furthermore, thanks to the research of AT
50 Florence, who first demonstrated the ability to formulate bilayer vesicles from non-ionic
51 surfactants, also known as non-ionic surfactant vesicles (NISVs) or niosomes (e.g. (Azmin et
52 al., 1985; Baillie et al., 1985; Uchegbu and Florence, 1995)), a range of other bilayer vesicles
53 have been developed. For example, vesicles built from surfactant polymers (e.g.
54 polymersomes (Okada et al., 1995)), cationic systems which can electrostatically bind DNA
55 (e.g. lipoplexes (Felgner et al., 1987)), vesicles incorporating bile salts to improve stability (e.g.
56 bilosomes (Conacher et al., 2001)), or virus components (e.g. virosomes (Almeida et al.,
57 1975)).

58 However, despite the substantial body of research investigating their use, the translation of
59 these bilayer vesicles into licensed products remains limited, with approximately 15 products
60 currently approved, including the first generic version of liposomal doxorubicin hydrochloride
61 (Lipodox). The approval of Lipodox by the US Food and Drug Administration (FDA) in priority
62 review was aimed to ensure that provision of doxorubicin hydrochloride liposomal injection
63 was not interrupted, despite supply shortages of the liposomal doxorubicin product Doxil
64 (licensed for the treatment of ovarian cancer). These supply shortages started in 2011 when
65 the FDA identified issues in the manufacturing site responsible for the production of Doxil.

66 In general, the manufacturing considerations of liposomal products can be considered a
67 notable hurdle, given the cost and relative complexity of their production. In terms of
68 characteristics and attributes to be considered for liposome drug products, these range from
69 the physico-chemical properties of all the individual components (include the drug substance,
70 the lipids and non-lipid components of the system) and the resulting liposomal product. Given
71 that the pharmacological, toxicological and pharmacokinetic properties of the drug can be
72 dictated by the liposomal product, quantification of the amount of drug incorporated and
73 retained within the system must be defined. Furthermore, given that the pharmacokinetic
74 profiles of the liposomal products are dictated by the liposomal physicochemical properties

75 (e.g. size, morphology, surface characteristics, liposome structure and integrity, net charge
76 etc.), these should be characterised and defined. Indeed these are key critical quality
77 attributes of a liposomal product and are often dictated by the method of manufacture.

78 Given the recent issues seen in the manufacture of liposome products and to facilitate the
79 transition of more liposomal products from bench to clinic, it is important that new, low-cost
80 and scalable manufacturing methods for liposomes and their related systems are developed.
81 At the basic level, there are two main ways of forming liposomes: either to produce large
82 vesicles and then employ size reduction methods (e.g. homogenisation, microfluidisation,
83 high-shear mixing and sonication), or alternatively bottom up methods, which promote the
84 formation of small vesicles from individual lipid monomers. Whilst the production of large
85 vesicles followed by size reduction is the commonly adopted method at the laboratory scale,
86 such methods of liposome manufacture lack industrial scalability and encapsulation
87 efficiencies are usually low.

88 In contrast, methods that exploit fluidic control to build liposomes from the bottom-up tend
89 to offer more industrial applicability. For example, the ethanol injection method was the first
90 one reported in the 1970s by Batzri and Korn (Batzri and Korn, 1973). Using this method, the
91 formation of liposomes results from the rapid injection of lipids dissolved in ethanol into an
92 aqueous buffer stream; the precipitation of the lipids leads to the formation of vesicles. This
93 method is relatively simple and easy to scale, with the process considerations including the
94 solubility of the lipids in the water-miscible solvent, rate of injection, and effective solvent
95 removal post-processing. Recent variations on this method include the adoption of inkjet
96 injection methods (Hauschild et al., 2005).

97 More recently, microfluidics has been considered for the formulation of liposomes (Jahn et
98 al., 2007; Kastner et al., 2014; Kastner et al., 2015). The application of microfluidic tools for
99 liposome manufacturing is based on the theory of a nanoprecipitation reaction resulting from
100 rapid mixing at the nanolitre scale (Song et al., 2008; deMello, 2006). In contrast to the top-
101 down methods for liposome manufacture, this nanoprecipitation can produce liposomes and
102 nanoparticles in a one-step process (Bally et al., 2012), with no further disruption of the
103 resulting liposomes required. The advantages of microfluidic-based technologies include
104 enhanced control over processing conditions, offering reproducible and robust

105 manufacturing of uniform liposome size distributions and, by working at reduced volumes
106 during development processes, costs can be reduced, whereas throughput is also increased
107 (Carugo et al., 2016; Jensen, 2001; van Swaay and deMello, 2013; Weibel and Whitesides,
108 2006). Furthermore, variations in flow rate and flow rate ratios allows for the engineering of
109 liposome-based systems in the range of 30 - 80 nm for small interfering RNA (siRNA) delivery
110 (Belliveau et al., 2012; Zhigaltsev et al., 2012), DNA (Kastner et al., 2014) and low solubility
111 drugs (Kastner et al., 2015). In the application of microfluidics for liposome manufacture,
112 there are a range of parameters to be considered (Figure 1) and testing and optimisation of
113 these parameters is important since they can impact on the critical product attributes of the
114 liposomal systems (e.g. Kastner et al., 2014). Parameters to be considered range from input
115 parameters – such as solvent selection, which can be influenced by lipid solubility – to
116 manufacturing parameters – such as chip design, flow rate of solvents through the chip and
117 the ratio they are mixed at, whilst temperature may also be a consideration (in the case of
118 high-transition temperature lipids). In terms of the chip design, micromixers can be classified
119 into active and passive mixers (Capretto et al., 2011). Passive micromixers require an input
120 from an external energy source, e.g. pressure-driven, temperature-induced or ultrasonic-
121 driven. In contrast, so called passive mixers do not require an additional external energy
122 source to achieve mixing, but use the fluid flow and specially designed micro-structures that
123 enhance diffusion and advection processes (Nguyen and Wu, 2004). In the production of
124 liposomes, a range of chip designs have been tested, including a staggered herringbone
125 micromixer based on patterns of grooves in the channel floor (Figure 1). The design introduces
126 a chaotic flow in a microchannel by subjecting the fluid to repetitive series of a rotational flow
127 profile, which is achieved by alteration of the grooves as a function of the axial position in the
128 channel (Stroock et al., 2002).

129 Within our laboratories we have already demonstrated the use of microfluidics to formulate
130 DNA-liposome complexes (Kastner et al., 2014) and incorporate low solubility drugs within
131 the bilayer of the liposomes (Kastner et al., 2015); however, the passive incorporation of a
132 hydrophilic drug has yet to be explored. Therefore, the aim of this current research is to build
133 on this knowledge, and demonstrate the use of microfluidics to prepare sub-100 nm
134 liposomes incorporating aqueous soluble drugs within their core. Furthermore, this study

135 investigate the preparation of liposomes co-entrapping both a hydrophilic and lipophilic drug
136 within the same formulation to promote co-delivery of drugs.

137

138 **2. Materials and methods**

139 **2.1. Materials**

140 Egg phosphatidylcholine (PC), 1,2-dimyristoylphosphatidylcholine (DMPC), 1,2-
141 dipalmitoylphosphatidylcholine (DPPC), 1,2-distearoylphosphatidylcholine (DSPC) were
142 purchased from Avanti Polar Lipids, Inc. (Alabaster, AL). Cholesterol was from Sigma-Aldrich
143 Company Ltd. (Poole, UK). Glipizide, metformin HCl and Phosphate buffered saline (PBS) in
144 tablet form (pH 7.4) were purchased from Sigma-Aldrich Company Ltd. (Poole, UK). All the
145 solvents used in the analysis were of analytical grade and were purchased from Fisher
146 Scientific UK (Loughborough, UK). Water used in the process of liposome preparation was of
147 milli-Q grade.

148

149 **2.2. Preparation of liposomes using microfluidics**

150 To prepare liposomes, the NanoAssemblr™ benchtop (Precision Nanosystems, Agronomy Rd,
151 Vancouver) was used with a 300 micron Staggered Herringbone Micromixer. Briefly, the lipids
152 at the appropriate ratio were dissolved in methanol. The aqueous buffer used in all studies
153 was PBS, 10 mM, pH 7.4. The flow rate ratio (FRR) between the aqueous and solvent stream
154 was varied from 5:1 to 1:1 (aq:solvent ratio) and the total flow rate (TFR) was varied from 5
155 to 15 mL/min. Through this method, liposome formation and incorporation of the drug(s) can
156 be performed simultaneously by addition of the drug into the appropriate phase; within these
157 studies, glipizide was dissolved in the solvent phase (1.1 mg/mL), whilst metformin was
158 dissolved in PBS prior to microfluidic mixing. The liposome formulations were collected from
159 the chamber outlet and dialysed at room temperature against PBS buffer for removal of
160 residual solvent and non-loaded drug.

161

162 **2.3. Liposome characterisation**

163 Dynamic light scattering (DLS) was used to determine the size, reported as Z-average (based
164 on intensity), and polydispersity index (PDI) of liposomes using Malvern NanoZS (Malvern
165 Instruments, Worcestershire, UK). Particle size was measured in PBS diluted 1 in 300, pH 7.4,
166 25 °C. The zeta potential was also measured using the Malvern NanoZS; based on the particle
167 electrophoresis principle in PBS, 1 mM, pH 7.4, 25 °C.

168

169 **2.4. Removal of solvent and non-incorporated drug**

170 3500-dalton dialysis tubing (Medicell membranes Ltd, London, UK) was used to remove
171 residual solvent and non-entrapped drug from the liposomal suspension. Prior to use, the
172 dialysis tubing was soaked under running water for two hours. Dialysis was performed using
173 PBS (composition: phosphate buffer 0.01 M, 0.0027 M potassium chloride and 0.137 M
174 sodium chloride, pH 7.4).

175

176 **2.5. Quantification of lipid recovery**

177 HPLC- ELSD (high performance liquid chromatography- evaporative light scattering detector)
178 was used to quantify the lipid recovery of liposomes produced by microfluidics at a 3:1 FRR
179 and 15 mL/min TFR. A Luna column (C18(2), 5 µm, dimensions 4.60 X 150 mm, pore size 100
180 Å) from Phenomenex (Macclesfield, UK) was used to detect the lipids. A 2 mL/min flow rate
181 was used with a twenty minute elution gradient, composed of solvent A (0.1% TFA in water)
182 and solvent B (100% methanol). During the first six minutes the gradient was 15:85 (A:B), at
183 6.1 minutes 0: 100 (A:B) and then back to the initial gradient of 15: 85 (A:B) from 15.1 to 20
184 minutes. The phospholipid and cholesterol lipids were analysed within the same run as they
185 have different elution times. The lipid recovery was calculated as a percentage in comparison
186 to the initial concentration of the stock solution.

187

188 **2.6. Quantification of non-entrapped and entrapped drugs**

189 Simultaneous quantification of metformin and glipizide (both liposome entrapped and non-
190 entrapped) was performed using reversed-phase high performance liquid chromatography
191 (RP-HPLC, Shimadzu 2010-HT, Milton Keynes, UK) connected with an ultra-violet detector at
192 233 nm to allow simultaneous quantification of both drugs. Isocratic elution was performed
193 using mobile phase of acetonitrile:PBS (65:35, pH 5.75) at constant flow rate of 1.0
194 mL/minute, using a Luna column (C-18, 5 μ , i.d. 150 X 4.6 mm) from Phenomenex
195 (Macclesfield, UK). A calibration curve produced from linear standards was used as reference
196 for the quantification of unknown. The calibration curved reported linearity (R^2) >0.995 and
197 all measurements were within the level of detection and level of quantification. Drug
198 incorporation is reported as % of initial amount used, and in all instances, overall recovery of
199 both drugs was also determined from amount entrapped and non-entrapped drug and was
200 between 90 to 110%.

201

202 **2.7. Drug release study**

203 The CE7smart USP-4 system (SOTAX AG, Switzerland) was used to create an incubating
204 environment for the release of drug encapsulated within liposomes. PBS (pH 7.4) was used in
205 a closed loop system and was circulated at constant temperature ($37 \pm 1^\circ\text{C}$) at a constant flow
206 of 8.0 mL/minute. Samples were withdrawn at time intervals of 10, 30, 60, 90, 120, 180, 360,
207 540, 720 and 1440 minutes. Drug release was quantified using RP-HPLC (described in section
208 2.6.) and reported as % release relative to amount of drug entrapped within liposomes.

209

210 **2.8. Cryo-TEM imaging of liposomes**

211 All the samples were freshly prepared on the day of analysis. Empty, single and co-drug loaded
212 liposomes were prepared using the method described before (section 2.2). A 3 μl aliquot of
213 each sample was placed onto a pre-cleaned lacey carbon coated grid and flash frozen by
214 plunging into liquid ethane cooled by liquid nitrogen. Samples were stored in liquid nitrogen
215 and conveyed to a cryo-holder and observed under the electron microscope at liquid nitrogen
216 temperatures. Grids were observed using Tecnai 12 G2 electron microscope (FEI, Eindhoven)

217 at 80 kV and the evaluation was performed in the magnification range of 40000 X to 135000
218 X.

219

220 **2.9. Statistical tools**

221 Unless stated otherwise, the results were calculated as mean \pm standard deviation (SD).
222 ANOVA followed by Tukey post hoc analysis was performed for comparison and significance
223 was acknowledged for p values less than 0.05. All the calculations were made using Graphpad
224 version-6 (GraphPad Inc., La Jolla, CA).

225

226 **3. Results**

227 **3.1 Solvent selection and lipid concentrations in the manufacture of liposomes using** 228 **microfluidics**

229 When establishing the process of liposome manufacture using microfluidics, one of the initial
230 input parameters to consider is the solvent selection. For appropriate mixing to occur, the
231 solvent needs to be miscible with the aqueous phase. Other factors dictating this solvent
232 selection are the lipid and drug compatibility and solubility in the selected solvent and
233 aqueous phase. To consider the effect of solvent selection, initial studies investigated the
234 preparation of 4 liposome formulations based on PC, DMPC, DPPC or DSPC mixed with
235 equimolar cholesterol (2:1 mass ratio). Results in Figure 2 demonstrate that solvent selection
236 plays an important role in the size of the formed vesicles; the combination of using methanol
237 for the lipid solvent and PBS as the aqueous phase produces liposomes in the smallest size
238 range, irrespective of the phospholipid used, with liposomes being approximately 70 to 100
239 nm in size. Replacement of methanol with ethanol in combination with PBS made no notable
240 difference to liposome size in the case of PC, DMPC or DPPC liposomes. However, in the case
241 of the DSPC:chol liposomes, preparing these vesicles using PBS and ethanol as the initial
242 solvents results in significantly ($p < 0.05$) larger vesicles that were well over 1000 nm in size.
243 Indeed, the DSPC formulation in general tended to be more sensitive to the initial solvent
244 selection, as switching from PBS to Tris buffer in combination with methanol also increased

245 the size of the DSPC:chol liposomes from 69 ± 3 nm to over 405 ± 63 nm (Figure 2). In general,
246 the polydispersity of the liposome formulation (as measured by the PDI) followed a similar
247 trend to the vesicle size, with the combination of methanol with PBS giving the most
248 homogeneous preparations.

249 The initial lipid amount in the solvent stream is also an important consideration in the
250 production of liposomes using microfluidics, with lower levels of lipids tending to promote
251 larger vesicles, as shown in Figure 3. However, working with initial amounts of lipid above 1
252 mg (3 mg/mL) produced vesicles around 100 nm or less with good lipid recovery (Figure 3)
253 and, irrespective of the lipid concentrations, varying the flow rate had no significant impact
254 on vesicle size (results not shown).

255

256 **3.2 Selection of flow rate and solvent to aqueous flow rate ratio**

257 Upon selection of the two base solvents (methanol with PBS), the next stage in the process
258 was to identify the effect of both the aqueous: solvent media (PBS:methanol) mixing ratio and
259 also the total flow rate; therefore, the flow rate ratio was varied from 1:1 through to 5:1 and
260 the total flow rate was varied from 5 to 15 mL per minute and the effect on the liposomal
261 attributes (size, PDI and zeta potential) were investigated. Given that these liposomes were
262 to be loaded with both an aqueous soluble drug (metformin) and a bilayer loaded drug
263 (glipizide), DSPC was selected as the phospholipid based on previous studies that
264 demonstrated longer chain lipids offer greater capacity to load drug within the bilayer of
265 vesicles (Mohammed et al., 2004; Ali et al., 2010; Ali et al., 2013) and retain drug within the
266 aqueous core (Gregoriadis and Davis, 1979). The cholesterol content was also reduced given
267 that a range of previous studies have shown that cholesterol is known to reduce aqueous
268 soluble drug leakage across the lipid bilayer (e.g. (Briuglia et al., 2015)), but also to potentially
269 inhibit drug incorporation in the liposomal bilayer (Ali et al., 2010; Mohammed et al., 2004).
270 Therefore, a DSPC: chol lipid weight ratio of 10:4 was selected to meet the needs of both good
271 aqueous drug retention and bilayer drug loading.

272 Results in Figure 4 demonstrate that a low aqueous:solvent ratio of 1:1 tended to produce
273 the largest vesicles, irrespective of the total flow rate, with liposomes being approximately

274 200 to 300 nm in size with PDI values of between 0.38 to 0.67. However, an increase in the
275 aqueous to solvent ratio to 3:1 reduced the vesicle sizes to approximately 120 – 130 nm, and
276 a further increase in the ratio to 5:1 reduced the vesicle size range to 80 to 90 nm with a PDI
277 range of 0.11 to 0.22, again with no notable effect of total flow rate being seen (Figure 4). In
278 all cases, the liposome formulations were near neutral in zeta potential as would be expected
279 for such formulations. From these studies, it can be seen that, across the range tested, the
280 flow rate ratio but not total flow rate had an impact on vesicle size; therefore, further studies
281 adopted a solvent to aqueous ratio of 5:1.

282

283 **3.3 Incorporation of aqueous and bilayer drug loading within liposomes manufactured by** 284 **microfluidics**

285 To investigate drug loading within both the aqueous and bilayer phases of liposomes,
286 metformin and glipizide were selected as model drugs, given their contrasting solubility and
287 their combined use in treating type-2 diabetes. In terms of initial drug added, 300 µg of
288 glipizide dissolved in methanol (the maximal amount soluble in the solvent phase used; 0.27
289 mL) along with the DSPC and cholesterol (2.7 mg and 1.1 mg, respectively), and 20 mg of
290 metformin was added to the PBS phase. Results in Figure 5 show that drug loading of glipizide
291 within the liposomal bilayer was approximately 40% and metformin entrapment was
292 approximately 20%. Furthermore, the results show that loading of the drug individually or in
293 combination had no significant impact on the loading capacity of the liposomes. However, the
294 presence of either drug in the formulation tended to push the vesicle size down by
295 approximately 20 nm, with the measured z-average particle size being 50 to 60 nm. The
296 bilayer vesicle constructs with and without the addition of these drugs as imaged by cryo-TEM
297 are shown in Figure 6; in all 4 cases, the formulations show a high proportion of small
298 unilamellar vesicles around 60 to 80 nm in size.

299 The effect of drug co-loading within the liposomal system on their relative release profiles
300 was also investigated (Figure 7). The majority of the *in-vitro* drug release studies are based
301 upon dialysis of liposomal formulation against large volumes of buffers or other simulated
302 media at physiological temperatures, and this excess buffer can lead to un-realistic gradients
303 across the liposomal membranes. Therefore, drug release was studied using USP-4 (flow

304 through cell (FTC) method), which has proved to be very versatile, with advantages of
305 operating pH gradients, achieving sink conditions for sparingly soluble drugs by use of
306 unlimited media volume and, most importantly for the current study, appropriateness for
307 micro-sized dosage forms, as it obviates sample aggregation. FTC enables dissolution
308 conditions to be achieved that are more representative of physiological conditions by
309 choosing the right flow rates, media type, media volume and cell preparation. Furthermore,
310 FTC is the most discriminating between formulation variants (Qureshi, S.A., 2006), whilst in
311 the closed loop system configuration, the dissolution media is re-circulated through the
312 sample contained in a flow through cell, producing a cumulative curve progression, with the
313 added advantage of a small volume in which dissolution takes place; the 22.6 mm-cell without
314 glass beads provides 19 mL capacity (Brown, W. 2005). The results show that, in both cases,
315 the drug incorporated individually had a slower release rate profile compared to the
316 liposomes containing both metformin and glipizide. For example, after 1 hour, liposomes
317 containing glipizide released 3% of the bilayer loaded glipizide; however, when metformin
318 was also present within the liposome formulation, glipizide release increased to 12%.
319 Similarly, after 1 hour metformin release increased from 35% to 64% when glipizide was
320 present in the bilayer (Figure 7), suggesting that co-loading of both drugs on the system had
321 an impact on the structural attributes of the liposomes.

322

323 **4. Discussion**

324 The use of microfluidics for the scalable production of liposomes allows for the cost-effective
325 and rapid production of liposomes. Despite increased research in exploring different
326 microfluidics parameters on liposome size, the effect of the organic solvent (used to dissolve
327 lipids) on liposome size has not been fully explored. During this microfluidics-based
328 manufacturing process, it has been proposed that the liposomes form as a result of the
329 alcohol and aqueous buffer mixing, thereby increasing the polarity of the solvent. This in turn
330 progressively decreases the lipid solubility, thereby promoting self-assembly into planar lipid
331 bilayers. As these planar bilayer discs grow, the surface area of hydrophobic chains exposed
332 to polar solvent around the perimeter of the disc will grow and increase the interfacial
333 tension. To circumvent this, the discs will bend and eventually close into spherical vesicles.

334 Most commonly, isopropyl alcohol has been used to dissolve lipids, with some studies using
335 the less toxic solvent, ethanol (Carugo et al., 2016). As shown in figure 2, despite all four lipids
336 being soluble in both methanol and ethanol, the organic solvent of choice affects the
337 liposome size attributes, potentially due to the differences in the self-assembly
338 rates/configurations of the discs and resultant vesicles. Previous investigations into use of
339 microfluidics to prepare liposomes (Zook and Vreeland, 2010) have shown that vesicle size is
340 modulated by temperature in the case of high-transition temperature lipids. The authors note
341 this to be due to the high membrane elasticity modulus associated with high transition
342 temperature lipids, with liposomes formed below or near the transition temperature of the
343 lipids tending to be larger. In contrast, liposomes formed at a temperature far above the
344 transition temperature have a much smaller dependence of size, where the membrane
345 elasticity modulus is relatively constant (Zook and Vreeland, 2010). Therefore, whilst
346 cholesterol is present in the formulations and could nullify the impact of the DSPC transition
347 temperature, during nanoprecipitation and formation of liposomes, these transition
348 temperatures may have an impact.

349 An additional issue with the use of ethanol may be that the residual presence of ethanol in
350 the liposome suspensions may also promote vesicle fusion; previous studies have shown that
351 increased ethanol concentration causes aggregation of liposomes produced by microfluidics
352 at a 1:1 FRR, and increasing the FRR to 3:1 removed the aggregation problem and formed
353 smaller liposomes (Maeki et al., 2015). Furthermore, the increased vesicle size may be a result
354 of the residual ethanol that may accumulate at the organic and aqueous interface (Patra et
355 al., 2006) thereby promoting vesicle fusion. Using computational studies to explore the effect
356 of methanol and ethanol on the DPPC lipid bilayer, Patra et al (2006) showed that ethanol
357 affects the structural properties of liposome bilayers, with this effect possibly more
358 prominent with the DSPC formulation due to the longer alkyl chains.

359 The results in Figure 4 show that manipulating flow conditions such as the speed at which
360 both streams, aqueous and organic, pass through the channels (TFR) did not affect the size of
361 the liposomes. On the other hand, the ratio between aqueous and organic phases (FRR) has
362 shown to be a key parameter in the control of the liposome size. This could be explained due
363 to the increase of aqueous volume that favours the formation of liposomes, since the lipid in
364 solvent is diluted (Jahn et al., 2004; Zook and Vreeland, 2010). Therefore, increasing FRR

365 produces a dilution effect, reducing amount of solvent (methanol in our case), and a faster
366 mixing. By this means the formation of larger liposomes by particle fusion and lipid exchange
367 is reduced (Zhigaltsev et al., 2012). In contrast, at low FRRs, the organic solvent is injected
368 into the system more slowly, allowing more time for both streams to interact, and therefore,
369 producing larger liposomes (Zhigaltsev et al., 2012). These results show that control of the
370 flow rate ratio can control vesicle size and that the rate of liposome production (in terms of
371 total flow rate) may be increased without impact on the liposome attributes.

372 In terms of drug loading within these vesicles prepared using microfluidics, the loading was
373 based on the principle of passive loading, where both drug and lipids are co-dispersed in the
374 aqueous phase. Generally, encapsulation efficiency for passive loading is less than 10% (Cullis
375 et al., 1989), whilst within our studies, we achieve notably higher hydrophilic (metformin)
376 drug loading of approximately 20% (Figure 5). The use of microfluidics has been suggested to
377 improve hydrophilic loading; For example, Jahn et al., 2008 reported unexpectedly high
378 entrapment efficiencies of a hydrophilic moiety (sulforhodamine B dissolved in PBS) within
379 nanometer-scale liposomes prepared using a continuous-flow microfluidics system. The
380 authors suggest that the high encapsulation efficiency may be due to a spatial concentration
381 enhancement induced by viscosity anisotropy in the microchannel (Jahn et al., 2008). In terms
382 of bilayer loading, the simultaneous packaging of the lipids and glipizide within the bilayer can
383 promote drug loading of approximately 40%, similar to our previous studies with propofol
384 (Kastner et al., 2015). The small decrease in size noted when liposomes were formed in the
385 presence of metformin and/or glipizide may be a result of changes in viscosity, miscibility
386 and/or mixing at the interphase as the liposomes form as discussed by Jan et al. (2008).

387 In terms of drug release, when both types of drugs are co-entrapped, our studies
388 demonstrated that they release faster than when individually encapsulated, suggesting an
389 interference or synergistic effect occurs. We hypothesised that the presence of glipizide
390 within the liposomal bilayer may interfere with the packing density of the lipids in the small
391 and highly curved bilayers and thereby increasing bilayer drug permeability. Furthermore, the
392 presence of metformin within the liposomes may also induce a concentration gradient across
393 the membrane, further driving the disruption of the bilayer, thereby simultaneously
394 increasing the release of both drugs.

395

396 **5. Conclusions**

397 Our results provide a concise analysis of liposome manufacturing using microfluidics.
398 Furthermore, for the first time we demonstrate the simultaneous entrapment of a hydrophilic
399 and a lipophilic drug (metformin and glipizide) using a scalable microfluidics system. Our
400 results demonstrate that microfluidics promotes greater hydrophilic and hydrophilic drug
401 loading compared to traditional methods, whilst critical factors to consider in the
402 manufacture of liposomes using microfluidics include the choice of solvent, lipid
403 concentration, and the flow rate ratio adopted during the microfluidics process. Therefore, it
404 can be concluded that microfluidics is a good alternative for liposome manufacturing.

405

406 **6. Acknowledgements**

407 This work was part funded by Aston University (SJ), the EPSRC Centre for Innovative
408 Manufacturing in emergent macromolecular therapies (EP/L015218/1) (MH) and
409 EP/I033270/1 (EK) and EU Horizon 2020 project TBVAC 2020 (Grant no. 643381) (CBR).

410

411 **Supporting information Available:** Data presented in this publication can be found at [DOI
412 XXXXXXXXXXXX to be provided at proofing stage].

413 **References**


- 414 Ali, M.H., Kirby, D.J., Mohammed, A.R., Perrie, Y., 2010. Solubilisation of drugs within liposomal
415 bilayers: alternatives to cholesterol as a membrane stabilising agent. *Journal of Pharmacy and*
416 *Pharmacology* 62, 1646-1655.
- 417 Almeida, J., Edwards, D.C., Brand, C., Heath, T., 1975. Originally published as Volume 2, Issue
418 7941FORMATION OF VIROSOMES FROM INFLUENZA SUBUNITS AND LIPOSOMES. *The Lancet* 306,
419 899-901.
- 420 Azmin, M.N., Florence, A.T., Handjani-Vila, R.M., Stuart, J.F.B., Vanlerberghe, G., Whittaker, J.S.,
421 1985. The effect of non-ionic surfactant vesicle (niosome) entrapment on the absorption and
422 distribution of methotrexate in mice. *Journal of Pharmacy and Pharmacology* 37, 237-242.
- 423 Baillie, A.J., Florence, A.T., Hume, L.R., Muirhead, G.T., Rogerson, A., 1985. The preparation and
424 properties of niosomes—non-ionic surfactant vesicles. *Journal of Pharmacy and Pharmacology* 37,
425 863-868.
- 426 Bally, F., Garg, D.K., Serra, C.A., Hoarau, Y., Anton, N., Brochon, C., Parida, D., Vandamme, T.,
427 Hadziioannou, G., 2012. Improved size-tunable preparation of polymeric nanoparticles by
428 microfluidic nanoprecipitation. *Polymer* 53, 5045-5051.
- 429 Bangham, A.D., Horne, R.W., 1964. Negative staining of phospholipids and their structural
430 modification by surface-active agents as observed in the electron microscope. *Journal of Molecular*
431 *Biology* 8, 660-IN610.
- 432 Batzri, S., Korn, E.D., 1973. Single bilayer liposomes prepared without sonication. *Biochimica et*
433 *Biophysica Acta (BBA) - Biomembranes* 298, 1015-1019.
- 434 Belliveau, N.M., Huft, J., Lin, P.J.C., Chen, S., Leung, A.K.K., Leaver, T.J., Wild, A.W., Lee, J.B., Taylor,
435 R.J., Tam, Y.K., Hansen, C.L., Cullis, P.R., 2012. Microfluidic Synthesis of Highly Potent Limit-size Lipid
436 Nanoparticles for In Vivo Delivery of siRNA. *Molecular Therapy. Nucleic Acids* 1, e37.
- 437 Briuglia, M.-L., Rotella, C., McFarlane, A., Lamprou, D.A., 2015. Influence of cholesterol on liposome
438 stability and on in vitro drug release. *Drug delivery and translational research* 5, 231-242.
- 439 Capretto, L., Cheng, W., Hill, M., Zhang, X., 2011. Micromixing Within Microfluidic Devices, in: Lin, B.
440 (Ed.), *Microfluidics: Technologies and Applications*. Springer Berlin Heidelberg, Berlin, Heidelberg,
441 pp. 27-68.
- 442 Carugo, D., Bottaro, E., Owen, J., Stride, E., Nastruzzi, C., 2016. Liposome production by microfluidics:
443 potential and limiting factors. *Scientific Reports* 6, 25876.
- 444 Conacher, M., Alexander, J., Brewer, J.M., 2001. Oral immunisation with peptide and protein
445 antigens by formulation in lipid vesicles incorporating bile salts (bilosomes). *Vaccine* 19, 2965-2974.
- 446 Cullis, P., Mayer, L., Bally, M., Madden, T., Hope, M., 1989. Generating and loading of liposomal
447 systems for drug-delivery applications. *Advanced drug delivery reviews* 3, 267-282.
- 448 deMello, A.J., 2006. Control and detection of chemical reactions in microfluidic systems. *Nature* 442,
449 394-402.
- 450 Felgner, P.L., Gadek, T.R., Holm, M., Roman, R., Chan, H.W., Wenz, M., Northrop, J.P., Ringold, G.M.,
451 Danielsen, M., 1987. Lipofection: a highly efficient, lipid-mediated DNA-transfection procedure.
452 *Proceedings of the National Academy of Sciences of the United States of America* 84, 7413-7417.
- 453 Gregoriadis, G., Davis, C., 1979. Stability of liposomes invivo and invitro is promoted by their
454 cholesterol content and the presence of blood cells. *Biochemical and Biophysical Research*
455 *Communications* 89, 1287-1293.
- 456 Gregoriadis, G., Ryman, B.E., 1971. Liposomes as carriers of enzymes or drugs: a new approach to
457 the treatment of storage diseases. *Biochemical Journal* 124, 58P.
- 458 Hauschild, S., Lipprandt, U., Rumpelcker, A., Borchert, U., Rank, A., Schubert, R., Förster, S., 2005.
459 Direct Preparation and Loading of Lipid and Polymer Vesicles Using Inkjets. *Small* 1, 1177-1180.
- 460 Jahn, A., Reiner, J., Vreeland, W., DeVoe, D., Locascio, L., Gaitan, M., 2008. UNEXPECTEDLY HIGH
461 ENTRAPMENT EFFICIENCIES IN NANOMETER SCALE LIPOSOMES WITH HYDRODYNAMIC FOCUSING

462 USING CONTINUOUS-FLOW MICROFLUIDICS, Twelfth International Conference on Miniaturized
463 Systems for Chemistry and Life Sciences.
464 Jahn, A., Vreeland, W.N., DeVoe, D.L., Locascio, L.E., Gaitan, M., 2007. Microfluidic directed
465 formation of liposomes of controlled size. *Langmuir* 23, 6289-6293.
466 Jahn, A., Vreeland, W.N., Gaitan, M., Locascio, L.E., 2004. Controlled vesicle self-assembly in
467 microfluidic channels with hydrodynamic focusing. *Journal of the American Chemical Society* 126,
468 2674-2675.
469 Jensen, K.F., 2001. Microreaction engineering—is small better? *Chemical Engineering Science* 56,
470 293-303.
471 Kastner, E., Kaur, R., Lowry, D., Moghaddam, B., Wilkinson, A., Perrie, Y., 2014. High-throughput
472 manufacturing of size-tuned liposomes by a new microfluidics method using enhanced statistical
473 tools for characterization. *International Journal of Pharmaceutics* 477, 361-368.
474 Kastner, E., Verma, V., Lowry, D., Perrie, Y., 2015. Microfluidic-controlled manufacture of liposomes
475 for the solubilisation of a poorly water soluble drug. *Int J Pharm* 485, 122-130.
476 Kumar, G.P., Rajeshwarrao, P., 2011. Nonionic surfactant vesicular systems for effective drug
477 delivery—an overview. *Acta Pharmaceutica Sinica B* 1, 208-219.
478 Maeki, M., Saito, T., Sato, Y., Yasui, T., Kaji, N., Ishida, A., Tani, H., Baba, Y., Harashima, H., Tokeshi,
479 M., 2015. A strategy for synthesis of lipid nanoparticles using microfluidic devices with a mixer
480 structure. *RSC Advances* 5, 46181-46185.
481 Mohammed, A., Weston, N., Coombes, A., Fitzgerald, M., Perrie, Y., 2004. Liposome formulation of
482 poorly water soluble drugs: optimisation of drug loading and ESEM analysis of stability. *International*
483 *journal of pharmaceutics* 285, 23-34.
484 Nguyen, N.-T., Wu, Z., 2004. Micromixers—a review. *Journal of Micromechanics and*
485 *Microengineering* 15, R1.
486 Okada, J.i., Cohen, S., Langer, R., 1995. In Vitro Evaluation of Polymerized Liposomes as an Oral Drug
487 Delivery System. *Pharmaceutical Research* 12, 576-582.
488 Patra, M., Salonen, E., Terama, E., Vattulainen, I., Faller, R., Lee, B.W., Holopainen, J., Karttunen, M.,
489 2006. Under the Influence of Alcohol: The Effect of Ethanol and Methanol on Lipid Bilayers.
490 *Biophysical Journal* 90, 1121-1135.
491 Pons, M., Foradada, M., Estelrich, J., 1993. Liposomes obtained by the ethanol injection method.
492 *International Journal of Pharmaceutics* 95, 51-56.
493 Song, Y., Hormes, J., Kumar, C.S.S.R., 2008. Microfluidic Synthesis of Nanomaterials. *Small* 4, 698-
494 711.
495 Stroock, A.D., Dertinger, S.K.W., Ajdari, A., Mezić, I., Stone, H.A., Whitesides, G.M., 2002. Chaotic
496 Mixer for Microchannels. *Science* 295, 647-651.
497 Uchegbu I.F., Florence, A.T., 1995. Non-ionic surfactant vesicles (niosomes): physical and
498 pharmaceutical chemistry. *Adv Colloid Interface Sci*, 58, 1-55.
499 van Swaay, D., deMello, A., 2013. Microfluidic methods for forming liposomes. *Lab on a Chip* 13,
500 752-767.
501 Weibel, D.B., Whitesides, G.M., 2006. Applications of microfluidics in chemical biology. *Current*
502 *Opinion in Chemical Biology* 10, 584-591.
503 Zhigaltsev, I.V., Belliveau, N., Hafez, I., Leung, A.K.K., Huft, J., Hansen, C., Cullis, P.R., 2012. Bottom-
504 Up Design and Synthesis of Limit Size Lipid Nanoparticle Systems with Aqueous and Triglyceride
505 Cores Using Millisecond Microfluidic Mixing. *Langmuir* 28, 3633-3640.
506 Zook, J.M., Vreeland, W.N., 2010. Effects of temperature, acyl chain length, and flow-rate ratio on
507 liposome formation and size in a microfluidic hydrodynamic focusing device. *Soft Matter* 6, 1352-
508 1360.

509


510

511 **Figure legends**

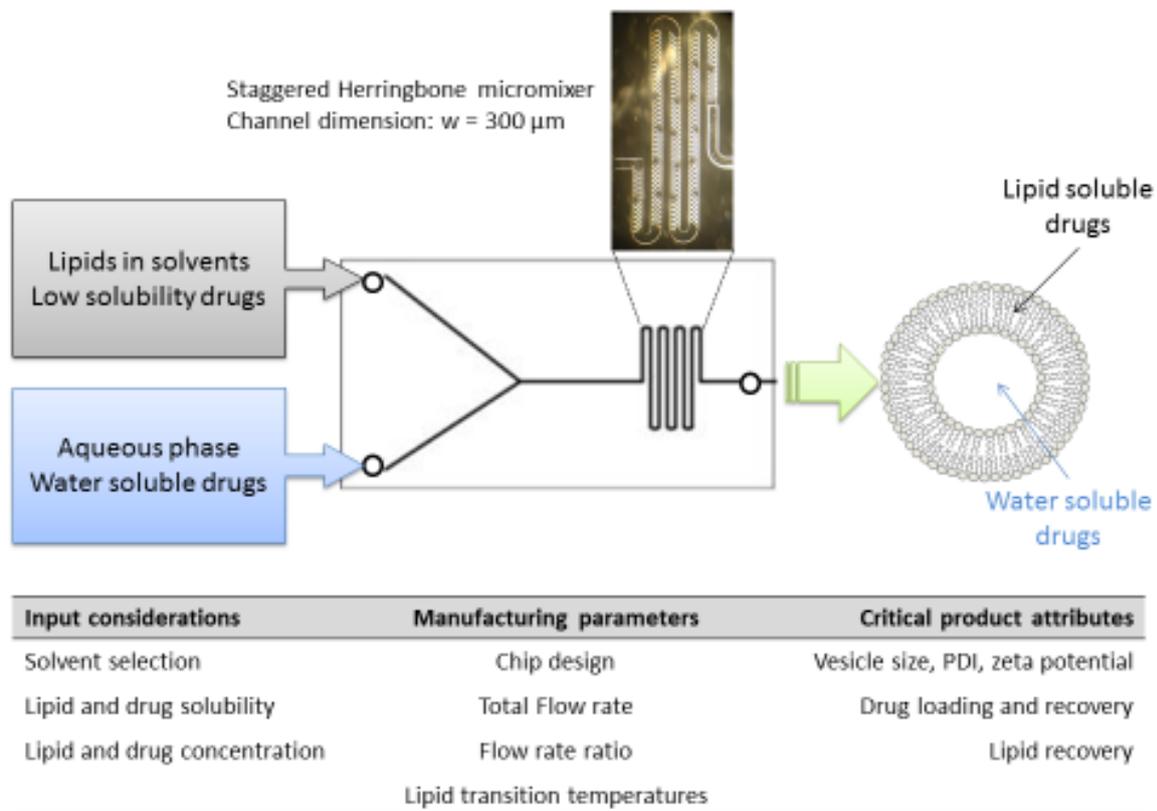

512 **Figure 1**

513 Figure 1: Liposomes produced by microfluidics – process and formulation conditions. In the
 514 production of liposomes using microfluidics, the lipids and lipophilic drugs are dissolved in
 515 an appropriate solvent and mixed with an aqueous phase containing water soluble drugs.
 516 These are mixed using micromixers that are available in a range of designs. Within these
 517 studies, a staggered herringbone micromixer was used. The rate of mixing of the aqueous
 518 and solvent buffer and the total follow rate are also parameters that require optimisation
 519 and the lipid concentration and lipid transition temperature may impact on this
 520 optimisation process. In terms of critical product attributes, key factors to consider include
 521 the liposome physico-chemical attributes (including size, pdi, zeta potential), drug loading
 522 and drug release profiles and lipid recovery.

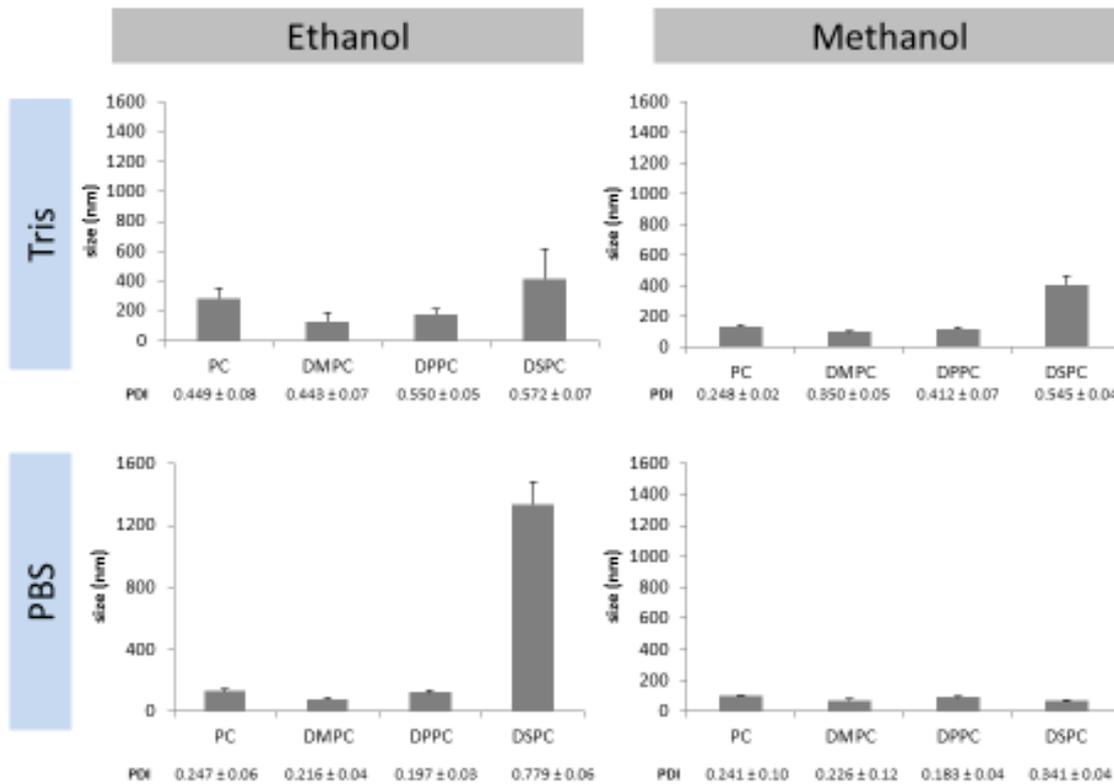

523 Figure 2:

524 Figure 2: The effect of solvent and buffer selection on liposomes prepared by microfluidics.
 525 Liposomes composed of PC, DMPC, DPPC, DSPC and cholesterol (1:1 molar ratio/2:1 mass
 526 ratio) were prepared by microfluidics at a 3:1 Flow rate ratio and 15 mL/ min Total Flow
 527 rate. Lipids were either dissolved in ethanol or methanol. Tris buffer or PBS were used as
 528 the aqueous phase, with size and PDI measured. Results are expressed as the means of
 529 three independent experiments ± SD.


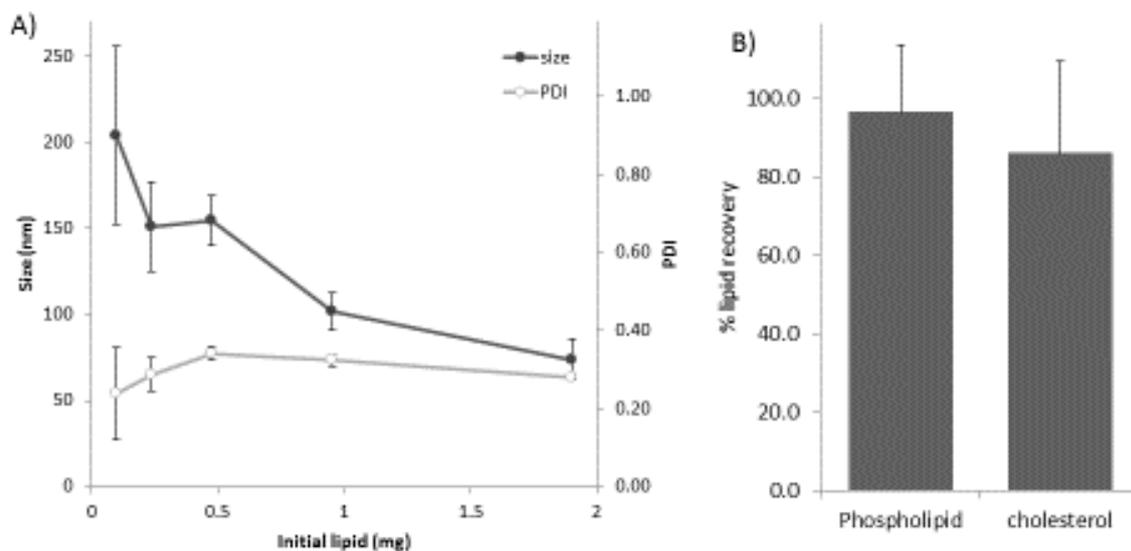



Figure 3.

530

531 Figure 3: Consideration of A) initial lipid amount and B) lipid recovery. Liposomes composed
 532 of PC and cholesterol (1:1 molar ratio/2:1 mass ratio) were prepared by microfluidics at a
 533 3:1 flow rate ratio using increasing amounts of initial total lipid, with size with size and PDI
 534 measured. Results are expressed as the means of three independent experiments \pm SD. For
 535 lipid recovery, results are averaged across a range of PC, DMPC, DPPC and DSPC in
 536 equimolar concentration with cholesterol. Results are expressed as the means of at least
 537 three independent experiments \pm SD.

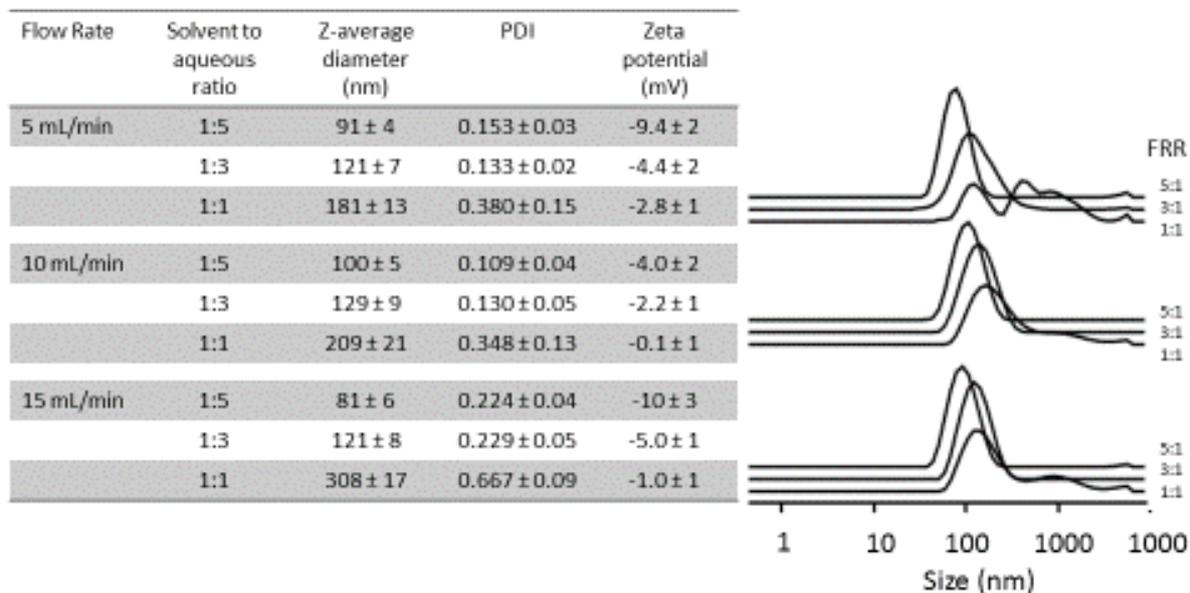


538 Figure 4.
 539 Figure 4: The effect on flow rate ratio and total flow rate on the liposomes z-average
 540 diameter, PDI and zeta potential of DSPE:cholesterol liposomes. Results represent mean ±
 541 SD, n = 4.
 542

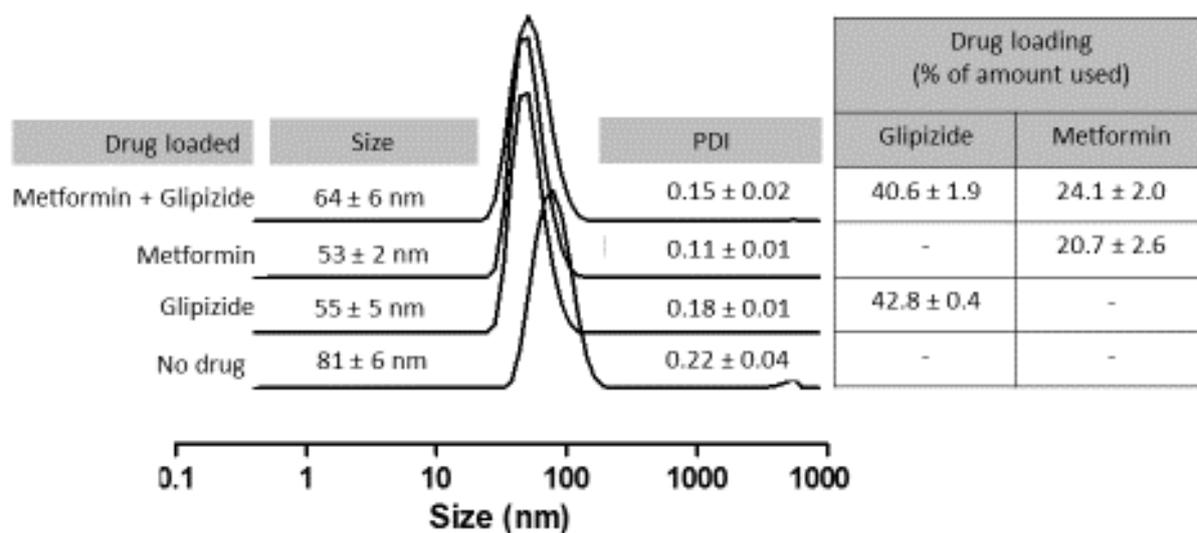

543 Figure 5

544 Figure 5: A comparison of DSPC:cholesterol liposomes z-average diameter, PDI and drug
 545 loading for small unilamellar liposomes with glipizide loading within the bilayer, with
 546 metformin loading within the aqueous phase, liposomes containing both glipizide and
 547 metformin and liposomes without drug present. Results represent mean ± SD, n = 4.

548

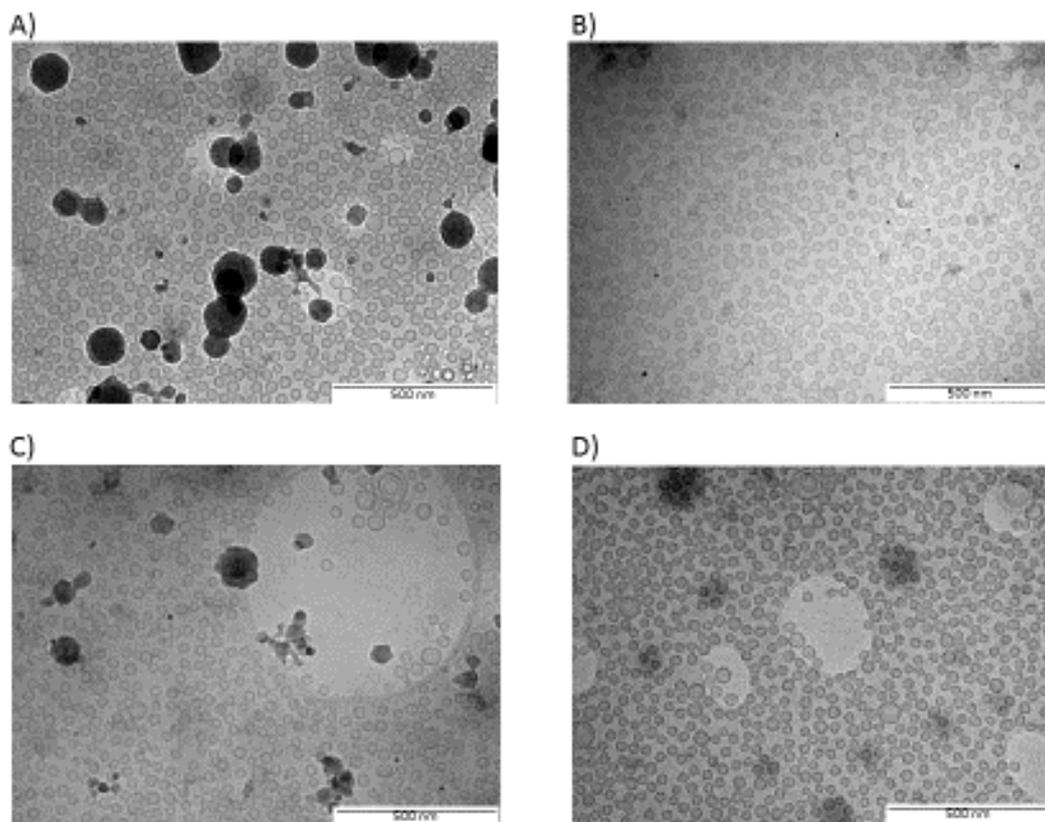

549 Figure 6

550 Figure 6: DSPC:Cholesterol liposomes produced by microfluidics at a 5:1 flow rate ratio and
551 15 mL/min and imaged using cryo-TEM. A) Liposomes without drug incorporated, B)
552 liposomes with glipizide loading within the bilayer, C) liposomes with metformin loading
553 within the aqueous phase D) liposomes containing both glipizide and metformin. The size bar
554 represents 500 nm.

555

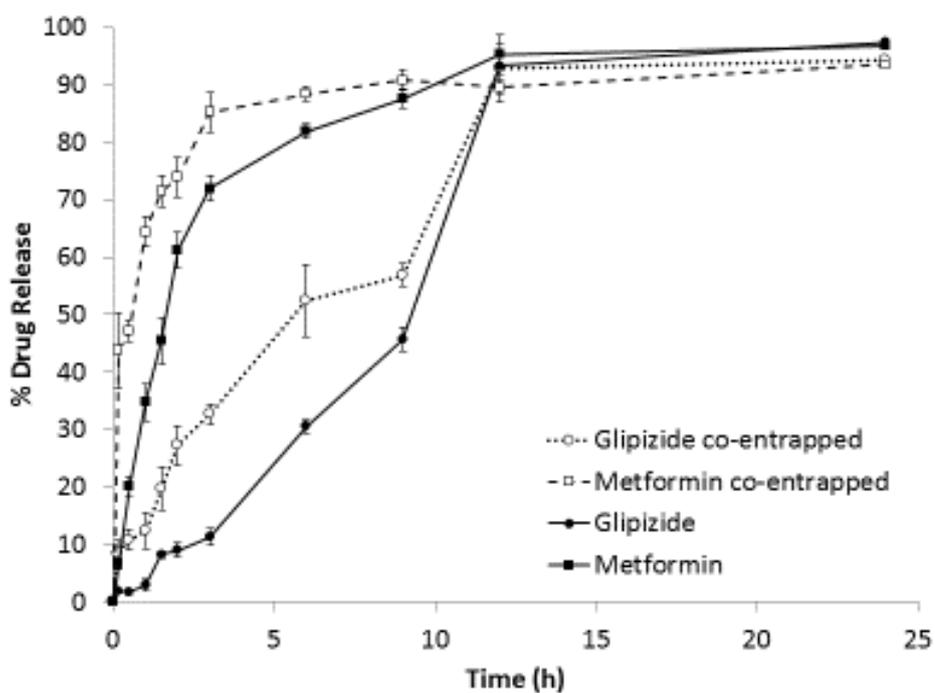


Figure 7.

556

557 Figure 7: Drug release profiles, measured using USP IV, from liposomes incorporating
 558 glipizide or metformin individually, or co-encapsulated within DSPC:chol liposome
 559 formulations produced via microfluidics as outlined in Figure 5. Release studies were
 560 undertaken with PBS (pH=7.4), temperature 37 °C and drug concentrations quantified by
 561 RP-HPLC. Results represent mean ± SD, n = 4.