



Finite element models, shakedown limit boundaries and load history applied.

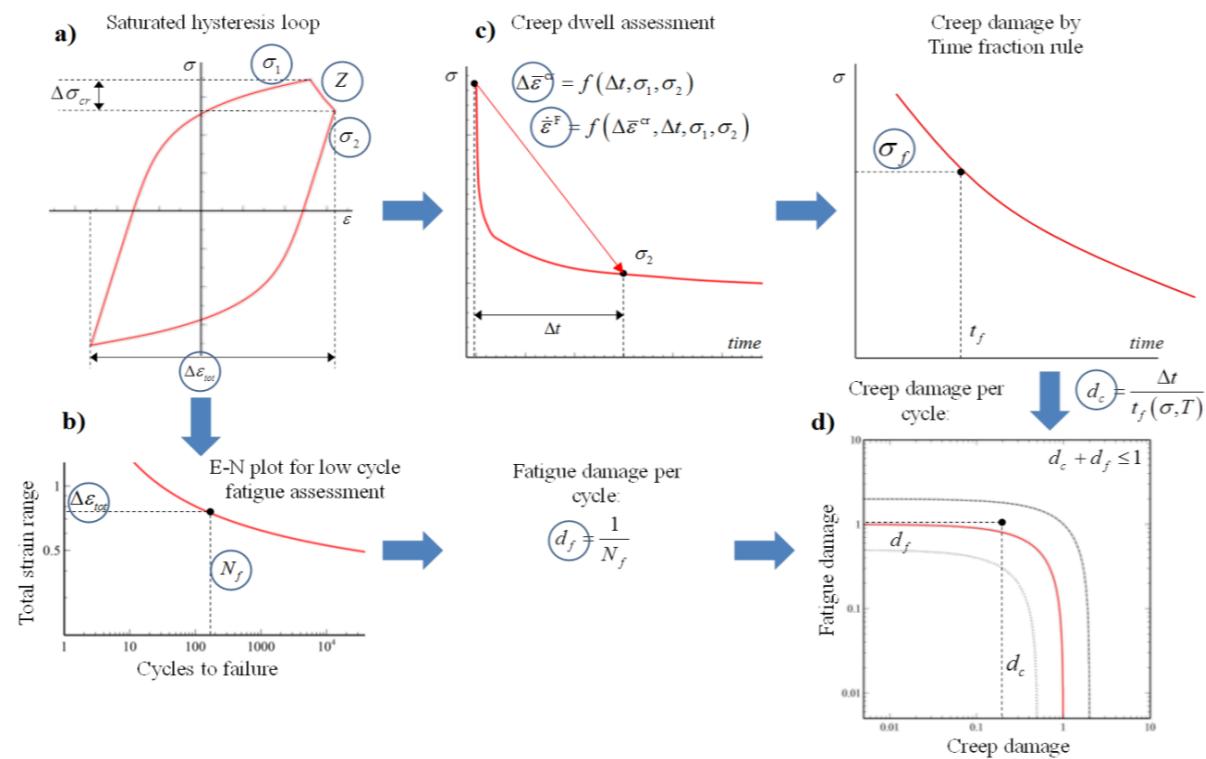

Creep fatigue assessment procedure adopted for crack initiation assessment.

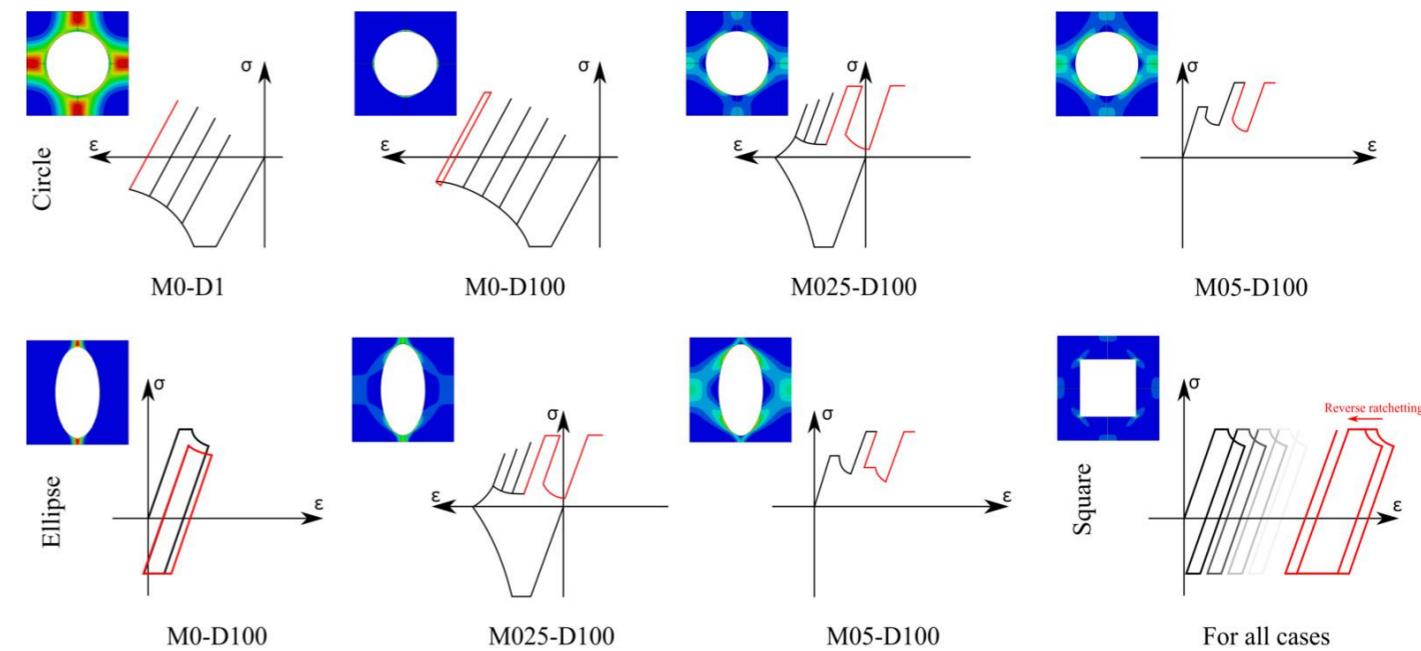

Reference transition hysteresis loops for the three cross-section studied.

Creep-fatigue and cyclically enhanced creep mechanisms in aluminium based Metal Matrix Composites

Dario Giugliano¹, Daniele Barbera², Haofeng Chen^{1*}, Nak-Kyun Cho¹, Yinghua Liu³

¹*Department of Mechanical & Aerospace Engineering, University of Strathclyde, Glasgow, G1 1XJ, UK*

²*School of engineering, University of Glasgow, Glasgow, G12 8QQ, UK*

³*Department of Engineering Mechanics, Tsinghua University, Beijing, 100084, China*

*Email: haofeng.chen@strath.ac.uk

Abstract

An aluminium (Al 2024T3) matrix composite reinforced with continuous alumina (Al₂O₃) fibres is investigated under tensile off-axis constant macro stress and thermal cyclic loading. The micromechanical approach to modelling and three different fibre cross-section geometries have been employed. The effect of creep is included by considering three dwell times at the peak temperature of the thermal loading history. The presence of the hold time gives rise to different sources of failure such as cyclic enhanced creep and creep ratchetting. These failure mechanisms are carefully discussed and assessed. The linear matching method framework has been used for the direct evaluation of the crucial parameters for creep-fatigue crack initiation assessment at the steady cycle. A detailed representation of the steady-state hysteresis loops is provided by using the strain range partitioning and a method for dealing with multiaxiality is reported with regard to the algebraic sign of the Mises-Hencky equivalent stress and strain. All the results obtained have been benchmarked by fully inelastic step-by-step (SBS) analyses. The design of a long fibre metal matrix composite should consider not only the detrimental effect of their dissimilar coefficient of thermal expansion, but also the state of stress at the interface between the matrix and fibre.

Keywords: Linear Matching Method (LMM); Cyclic Plasticity; Low Cycle Fatigue (LCF); Creep-Fatigue Interaction; Metal Matrix Composite (MMC).

1 Introduction

Metal matrix composites (MMCs), are undergoing rapid development to keep up with the requirements of aerospace and automotive industrial sector applications where minimal weight, and increased efficiency are critical factors (Cantor et al., 2003). Predicting composite behaviour under hostile and demanding environments due to the combined action of thermal and mechanical loading, allow for much more effective and reliable use of these complex materials. When a temperature hold time within the cyclic thermal loading is imposed, a combination of thermal fatigue and creep damage occur inside the matrix. Creep produces intergranular cavitation damage that is strongly affected by the hold time's position within the loading cycle. If the creep dwell starts at the pick of the tensile stress, intergranular damage occurs even for short hold times. Fatigue failure instead is a multi-stage process. It begins with the initiation

of cracks and with continued cyclic loading the cracks propagate through transgranular paths, with surface striations and wide surface cracks.

In engineering components operating at high temperature, creep lifetime can be significantly reduced when a cyclic mechanical loading is superimposed in the creep regime. Four types of damage's interactions can occur i.e. pure fatigue, transgranular competing, mixed interaction and pure creep (Barbera et al., 2016b), depending on strain range and dwell time (Hales, 1980; Plumbridge, 1987). A better understanding of the micro material scale is necessary to ensure that certain types of failure mechanism do not arise, such as low cycle fatigue (LCF) crack initiation, ratchetting, cyclically enhanced creep or creep ratchetting. This involves the determination of the shakedown limit, ratchet limit, plastic strain range for LCF assessment, and creep cyclic plasticity interaction (Barbera et al., 2016b; Giugliano et al., 2017; Giugliano and Chen, 2016). The schematic representation of the stress-strain material response due to cyclic loading with creep dwell at the tensile peak, as reported in (Barbera et al., 2016b), clarifies the importance of the aforementioned design limits. Indeed when the load level is below the elastic limit, no plastic strain occurs at the first cycle and the subsequent creep stress relaxation does not cause any plasticity during the following unloading and loading phases. Plasticity at the first cycle occurs when the load point is above the elastic limit. Here different scenarios can take place depending upon the load level i.e. the effect of primary and secondary loads, and dwell time. If the load level is largely below the shakedown limit and the dwell time is short enough, the stress relaxation during the subsequent creep hold times is not significant; hence no plastic strain occurs during the subsequent cycles. The steady-state response is similar to shakedown and the accumulated creep damage is identical to the monotonic load case. Instead for a higher load level in the shakedown zone but close to the shakedown limit, creep enhanced plasticity can occur which lead to either cyclically enhanced creep or creep ratchetting (EDF Energy, 2014). Two scenarios are possible when cyclically enhanced creep occur depending upon the magnitude of the primary and secondary loads. For both cases, a steady-state closed loop response appears either with only creep strain in loading or with both plastic strain and creep strain in loading. As a closed loop is expected, the inelastic strain in loading is compensated by the reverse plasticity in unloading. Compared to the monotonic load, more severe creep-fatigue damage arises. When the inelastic strain in loading is not compensated by the plastic strain in unloading, a mechanism known as creep ratchetting is expected (Chen et al., 2014). Ratchetting is a cyclic phenomenon, which result in the progressive accumulation of plastic strain. From Bree (Bree, 1967), it is known that for general thermomechanical cyclic loading without hold time, if the structure operates in a region of strict or global shakedown no inelastic strain accumulation occurs. This statement, as discussed previously, becomes imprecise when stress relaxation due to creep dwell arises. Indeed, if within the shakedown zone, particular conditions in terms of load level and hold time are satisfied, either cyclically enhanced creep or creep ratchetting occurs.

The effects of pure thermal fatigue with constant off-axis mechanical load (Chen and Ponter, 2005; Giugliano et al., 2017; Giugliano and Chen, 2016; Jansson et al., 1994; Jansson and Leckie, 1992; Ponter and Leckie, 1998a, b) and thermo-mechanical fatigue (TMF) with hold time (Barbera et al., 2016a; Bettge et al., 2007; Halford et al., 2000; Hertz-Clemens et al., 2002; Mirdamadi and Johnson, 1996; Mondali et al., 2005; Nicholas et al., 1996; Rutecka et al.,

2011) on MMCs have been under the attention of the authors over the last five years . The aim of this work is to investigate the impact of three different fibre cross-section geometries i.e. circular cross-section, elliptical cross-section and square cross-section on the creep-fatigue interaction behaviour of continuous fibre reinforced aluminium matrix composites (CFAMCs). For the loading conditions investigated, the stress state at the matrix-fibre's interface, gives rise to a new ratchetting mechanism which affects the cyclic stress-strain hysteresis loop of CFAMCs. Indeed, by superimposing a cyclic thermal load with dwell time over an off-axis constant macro stress, a scenario where mechanical and thermal stresses at the matrix-fibre's interface act in the opposite direction can occur. In this situation, the effect of both stress relaxation and residual stress field can lead the structure to experience creep ratchetting with a total open hysteresis loop (TOL). This work, will explore the damaging effect of this new mechanism which has been neglected in (Barbera et al., 2016a, b). A great number of numerical simulations are required to study different geometries, with each being subjected to a variety of loading conditions and dwell times. For this reason the traditional Abaqus (Abaqus, 2013) incremental finite element approach is not a viable option due to the large computational cost. In order to perform an accurate and efficient analysis the Linear Matching Method (LMM) is used in this work, which has been demonstrated to be capable of providing solutions for different classes of problems (Chen, 2010; Chen et al., 2014; Chen and Ponter, 2010; Giugliano et al., 2017; Giugliano and Chen, 2016; Gorash and Chen, 2013; Xuanchen Zhu, 2017). Recently the extended LMM Direct Steady Cyclic Analysis (eDSCA) has been adopted by the authors to perform a preliminary study on the creep and fatigue response of a MMCs unit cell (Barbera et al., 2016a), further demonstrating the method's applicability. Although the numerical results presented require extensive experimental verifications before they can be generally adopted, the features were chosen on the basis of the reasonableness of their prediction in several cases where they could be anticipated with some confidence (EDF Energy, 2014).

2 Numerical method

In order to calculate the steady-state cycle response of a structure subjected to an arbitrary cyclic load history, a numerical procedure based on the minimization process of $I(\dot{\epsilon}_{ij}^c) = \sum_{l=1}^L I^l$ has been developed (Chen et al., 2014; Chen and Ponter, 2006) and further tested (Barbera et al., 2016a; Gorash and Chen, 2013). This function is related to a class of kinematic admissible strain rate $\dot{\epsilon}_{ij}^c$, defined for a L total number of loading instances. An incremental form has been proposed for the minimization function as follow:

$$I^l(\Delta\epsilon_{ij}^l) = \int_V \left\{ \sigma_{ij}^l \Delta\epsilon_{ij}^l - [\hat{\sigma}_{ij}^l(t_l) + \rho_{ij}^l(t_l)] \Delta\epsilon_{ij}^l \right\} dV \quad (1)$$

Where σ_{ij}^l is the cyclic stress calculated at load instance “ l ”, $\Delta\epsilon_{ij}^l$ is the inelastic strain increment, and $\hat{\sigma}_{ij}^l(t_l)$ is the linear elastic stress associated to the cyclic history considering cyclic and constant loading and $\rho_{ij}^l(t_l)$ is the residual stress at each load instance. This residual stress is calculated by the sum of the constant part of the changing residual stress $\bar{\rho}_{ij}$ and the summation of all the previous changing residual stress field increments $\Delta\rho_{ij}(t_l)$. This incremental

formulation allows the strain rate history $\dot{\varepsilon}_{ij}^c$ to be replaced with a sequence of increments of strain $\Delta\varepsilon_{ij}^l$, which occur during the load cycle at each time t_l . The eDSCA is capable of calculating, by iterative mean, the inelastic strain increment $\Delta\varepsilon_{ij}^l$, which minimize the function shown in equation (1). A total of K sub-cycles are requested to reach the convergence. Within each k sub-cycle a total of L load increments need to be performed. The residual stress field and inelastic strain increment associated to each load instance l are obtained. At each increment the residual stress and inelastic strain are calculated by the elastic stress and the previous accumulated residual stresses. When the load instance does not contain a creep dwell, the plastic strain increment $\Delta\varepsilon_{ij,k+1}(t_l)'$ can be calculated by:

$$\Delta\varepsilon_{ij,k+1}(t_l)' = \frac{1}{2\bar{\mu}(t_l)} \left[\hat{\sigma}_{ij}(t_l) + \rho_{ij,k+1}(t_{l-1}) + \Delta\rho_{ij,k+1}(t_l) \right] \quad (2)$$

where notation (') refers to the deviator component of stresses and $\bar{\mu}$ is the iterative shear modulus (Chen et al., 2014), $\hat{\sigma}_{ij}$ is the associated elastic solution, $\rho_{ij,k+1}(t_{l-1})$ is the prior changing residual stress history and $\Delta\rho_{ij,k+1}(t_l)$ is the residual stress associated to the inelastic strain increment. If required, the calculated plastic strain is used to iteratively change the yield stress in the upcoming $k+1$ sub-cycle, considering the Ramberg-Osgood (RO) (Skelton et al., 1997) material response. The Ramberg-Osgood model is based on the interpolation of cyclic data at different strain range at the steady state (saturated cycle). The combination of all these points' forms the well-known "locus of the tips" (Hales et al., 2002). This approach allows considering the stabilised loop, at different strain range, for cyclic hardening or softening materials, however does not consider the evolution of the cyclic response of the structures that is considered negligible.

In load cases where creep is present, the equivalent creep strain increment $\Delta\bar{\varepsilon}^c$ is calculated by the following equation for the associated dwell time Δt using the Norton-Bailey relation:

$$\Delta\bar{\varepsilon}^c = \frac{B(n-1)\Delta t^{m+1}(\bar{\sigma}_s - \bar{\sigma}_c)}{\left(\frac{1}{\bar{\sigma}_c^{n-1}} - \frac{1}{\bar{\sigma}_s^{n-1}}\right)(m+1)} \quad (3)$$

where B, m and n are the creep constants of the material. $\bar{\sigma}_c$ represents the creep flow stress, which is the sum of the start-of-dwell stress $\bar{\sigma}_s$ and the residual stress $\Delta\rho_{ij}^c$ caused by the dwell period. The creep flow stress is then determined by accurately evaluating the creep strain rate $\dot{\varepsilon}^F$ at the end of the dwell time:

$$\bar{\sigma}_c = \left(\frac{\dot{\varepsilon}^F}{B\Delta t^m} \right)^{\frac{1}{n}} \quad (4)$$

$$\dot{\varepsilon}^F = \frac{\Delta\bar{\varepsilon}^c}{\Delta t} \frac{(m+1)}{(n-1)} \frac{\bar{\sigma}_c^n}{(\bar{\sigma}_s - \bar{\sigma}_c)} \left(\frac{1}{\bar{\sigma}_c^{n-1}} - \frac{1}{\bar{\sigma}_s^{n-1}} \right)$$

The remaining part of the procedure calculates the residual stress at each increment through the solution of linear problems. The residual stress field and the iterative shear modulus obtained are updated for the next cycle $k+1$ for each load instance t_l by adopting the linear matching equation;

$$\bar{\mu}_{k+1}(x, t_l) = \bar{\mu}_k(x, t_l) \frac{\sigma_y^R(x, t_l)_k}{\bar{\sigma}(\hat{\sigma}_{ij}(x, t_l) + \rho_{ij}^r(x, t_l)_k)} \quad (5)$$

where $\bar{\mu}_k(x, t_l)$ is the iterative shear modulus at the sub-cycle k for l^{th} load instance. $\sigma_y^R(x, t_l)_k$ is the iterative yield stress for RO material model or yield stress for the Elastic Perfectly Plastic material model at load instance t_l . The yield stress $\sigma_y^R(x, t_l)_k$ will be replaced by creep flow stress $\bar{\sigma}_c$ if creep relaxation occurs at the load instance. $\rho_{ij}^r(x, t_l)_k$ is the sum of the constant residual stress field and all the previous changing residual stresses at different load instances. This procedure is capable of characterizing the whole steady-state cycle calculating both plastic and creep response and considering their combined effects. Once the entire numerical process is converged the creep fatigue endurance can be evaluated. The required key parameters for the assessment can be accurately calculated from the stabilised hysteresis loop by adopting the procedure depicted in **Figure 1** and it is based on the procedure developed by (Wada et al., 1997). The fatigue and creep damage are accounted separately by the evaluating the total strain range, the stress at the start of creep dwell, the stress drop, the average creep rupture stress and creep strain accumulated during the dwell. In addition, compressive creep dwells are identified and neglected to avoid introducing overly conservative assessments.

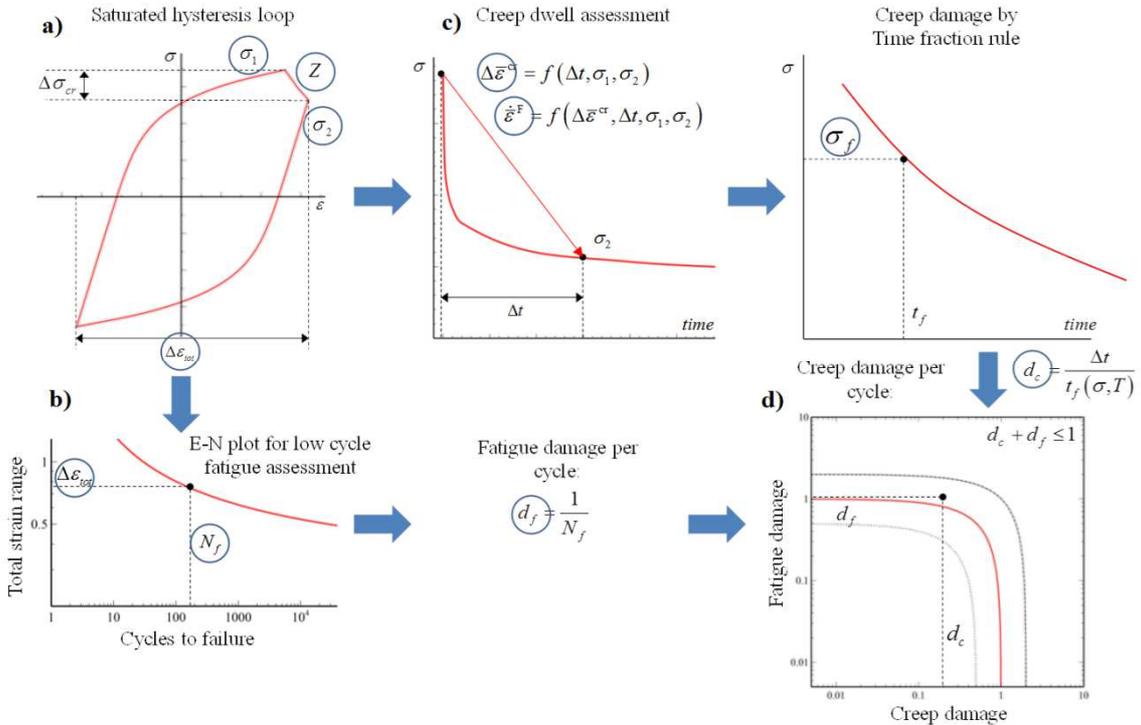


Figure 1 Creep fatigue assessment procedure adopted for crack initiation assessment. a) The saturated hysteresis loop is characterized by the eDSCA, b) the total strain range is used to estimate the number of cycle to failure due to fatigue and the associated damage per cycle, c) the creep dwell is assessed determining the damage per cycle, d) the total damage is calculated.

3 Problem description and finite element models

The modelling strategy employed for this study, relies on the micromechanical approach where, in the presence of material nonlinearity, the anisotropic composite behaviour is predicted by using constitutive models for the isotropic constituent materials (Aboudi et al., 2012). The same modelling strategy has been used in our previous paper where the authors investigated the effect of fibre cross-section geometry on the cyclic plastic behaviour of fibre reinforced MMCs (Giugliano et al., 2017).

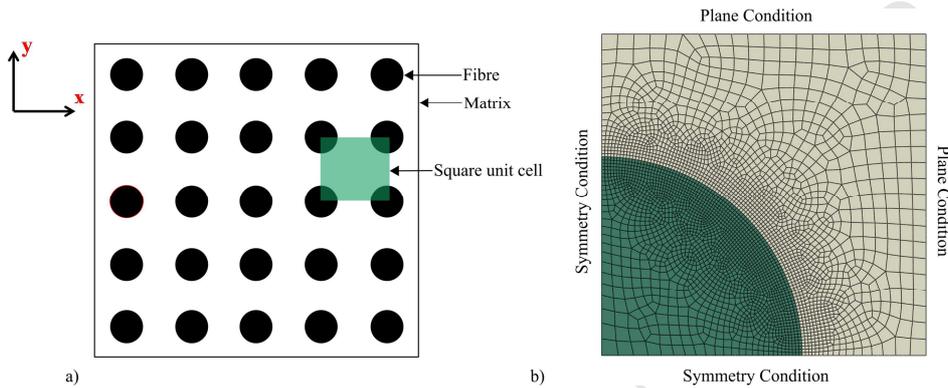


Figure 2 a) Square packing pattern, b) Quarter of the unit cell with applied boundary conditions.

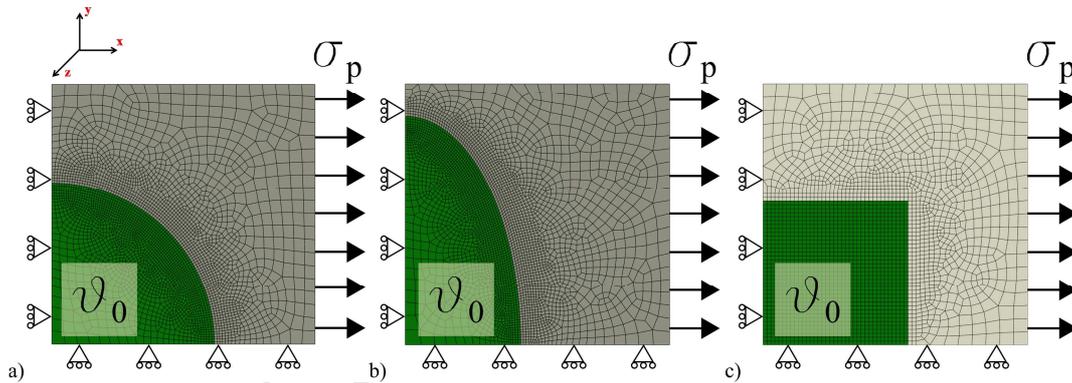


Figure 3 Finite element models for the a) circular cross-section, b) elliptical cross-section and c) square cross-section.

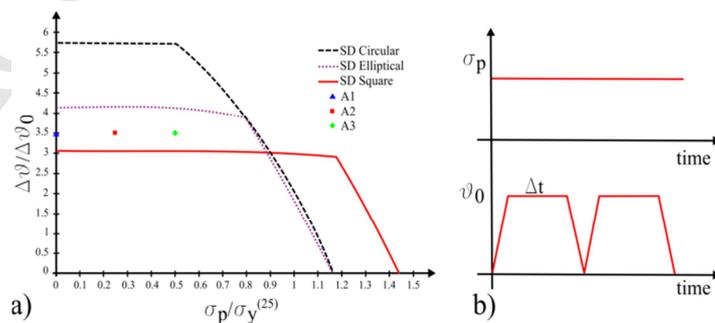


Figure 4 a) Shakedown limit boundaries for the three cross-section geometries analysed under constant mechanical load and cyclic thermal loading without dwell time, b) load history applied with dwell time related to the point A1, A2, and A3.

Here, three geometries have been considered: circular cross-section, elliptical cross-section and square cross-section, all arranged in a square packing pattern (**Figure 2a**). Plane strain assumption is suitable for such application as the dimension in the direction of the fibre, referred to as direction z , is much larger than the other two. Therefore, strain components ε_{xz} , ε_{yz} and ε_{zz} are equal to zero at any time. Due to the symmetry, only a quarter of the unit cells have been considered (**Figure 3**). Therefore, symmetry conditions along with plane conditions, applied by Abaqus constraint equations, have been imposed (**Figure 2b**). The meshes are composed respectively by 3507, 3692 and 2326 8-node biquadratic plane strain quadrilateral elements, with a reduced integration scheme. This modelling strategy is suggested in (Chen and Hachemi, 2014), when a stress approach is considered on the local scale. Indeed, for stress approach, beside the uniform stress imposed on the boundary, one degree of freedom of the boundary is coupled in order to maintain the periodic deformation. Despite periodic boundary conditions are more realistic, both stress approach and strain approach provide a consistent deformation of the boundary (Chen and Hachemi, 2014).

An aluminium matrix (Al 2024T3) reinforced with 30% of alumina (Al_2O_3) is considered. A viscoplastic model without cyclic hardening simulates the former while a perfectly elastic model simulates the latter. The fibre has a Young's modulus (E) of 370 GPa, a Poisson's ratio (ν) of 0.26, a coefficient of thermal expansion (CTE) of $8 \times 10^{-6} \text{ }^\circ\text{C}^{-1}$ and a ultimate tensile strength (UTS) 5000 MPa while the matrix has a Young's modulus of 73 GPa, a Poisson's ratio of 0.33, a coefficient of thermal expansion of $23 \times 10^{-6} \text{ }^\circ\text{C}^{-1}$ and the temperature dependent yield stress is reported in **Table 1**.

Table 1. Temperature dependent yield stress for 2024T3 aluminium alloy.

| | 25°C | 150°C | 175°C | 200°C |
|------------------|------|-------|-------|-------|
| σ_y [MPa] | 371 | 351 | 322 | 315 |

Due to the temperature considered, it is relevant to evaluate the creep strain only for the aluminium matrix. The creep constitutive equation adopted is the Norton-Bailey law:

$$\dot{\varepsilon}^{cr} = A \cdot \sigma^n \cdot t^m \quad (6)$$

where n is the stress exponent, m is the time exponent for the primary creep stage and A [$\text{MPa}^{-n} \times \text{h}^{-(m+1)}$] is the power law multiplier, the tensile creep data are taken from (Maximov et al., 2014) and reported in **Table 2**.

Table 2. Creep parameters A , n and m for 2024T3 aluminium alloy.

| | 150°C | 175°C | 200°C |
|-----|------------------------|------------------------|------------------------|
| A | $0.763 \cdot 10^{-12}$ | $3.461 \cdot 10^{-12}$ | $4.079 \cdot 10^{-12}$ |
| n | 3.246 | 3.299 | 3.395 |
| m | -0.303 | -0.573 | -0.535 |

In order to explore the effect of different fibre cross-section geometry on the creep-fatigue response, shakedown boundaries for the models in **Figure 3**, which are related to the previous study are considered and shown in **Figure**

4a. The axes are expressed in non-dimensional variables $\sigma_p/\sigma_y^{(25)}$ and $\Delta\theta/\Delta\theta_0$ where $\sigma_y^{(25)} = 371\text{MPa}$ is the yield stress at 25°C while $\Delta\theta_0 = 50^\circ\text{C}$ is the reference temperature load range. A uniaxial macro-stress $\sigma_p = 371\text{MPa}$ is applied in a direction perpendicular to opposing faces of the unit cells and is maintained constant while a cyclic temperature field with hold time Δt is applied uniformly over the unit cells, with a varying range from 0°C to $\Delta\theta_0$ (**Figure 4b**). Three load points are investigated and shown in **Figure 4a** i.e. $A_1(0, 3.5)$, $A_2(0.25, 3.5)$ and $A_3(0.5, 3.5)$, which represent shakedown for both the circular cross-section and the elliptical cross-section and reverse plasticity for the square cross-section when the applied cyclic loading condition does not have the hold time Δt (**Figure.3** of (Giugliano et al., 2017)). By introducing a high temperature dwell time as shown in **Figure 4b**, creep enhanced plasticity may occur (Barbera et al., 2016a) as discussed in section 1. In order to explore the influence of the dwell time on the steady-state behaviour of MMCs, each load point is investigated for three different dwell times i.e. 1 hour, 10 hours, 100 hours referred to as D1, D10, D100 within the paper.

When the authors performed this study, no low cycle fatigue data for Al2024T3 was available at high temperature, this is often the case and in most cases do not cover all the operating conditions required for an assessment procedure. For this reason a robust and efficient method was created by (Coffin Jr, 1954; Manson, 1954; Manson, 1968; Muralidharan and Manson, 1988) and further modified. The key concept of these methods is to estimate the fatigue life from common tensile test. If creep has to be considered, creep rupture test are also used. Such approach is based on the possibility to separate the LCF plot into two strain components the elastic and plastic one. Using the following relationship for the elastic $\Delta\varepsilon_{el}$ and plastic strain $\Delta\varepsilon_{pl}$ range:

$$\Delta\varepsilon_{el} N_f^{\alpha_1} = C_1 \quad (7)$$

$$\Delta\varepsilon_{pl} N_f^{\alpha_2} = C_2 \quad (8)$$

where α_1 and α_2 are material properties related to the slopes, and C_1 and C_2 are related to the fatigue ductility. By combining equation (7) and (8) the Coffin-Manson relationship is derived, which relates the total strain range $\Delta\varepsilon_{tot}$ with the number of cycles to fail N_f .

$$\frac{\Delta\varepsilon_{tot}}{2} = \frac{\sigma_f'}{E} \cdot (2N_f)^b + \varepsilon_f' \cdot (2N_f)^c \quad (9)$$

The right hand part of (9) represents respectively the elastic strain range and the plastic strain range, where the coefficient σ_f' is related to the material fatigue strength, instead ε_f' is the material fatigue ductility strength. Manson and others developed and modified equation (9) obtaining the ‘‘Universal Slope Method (USM)’’ (Manson, 1965; Muralidharan and Manson, 1988) assuming that the slopes coefficient b and c are constants. Furthermore, the

equations for σ_f' and ε_f' have been developed and proposed by Manson in his work (Manson, 1965) defining the total strain range as follow:

$$\frac{\Delta\varepsilon_{tot}}{2} = \frac{\sigma_f'}{E} \cdot (2N_f)^b + \varepsilon_f' \cdot (2N_f)^c \quad (10)$$

The fatigue strength coefficients and the fatigue ductility are calculated using the following equations:

$$\begin{aligned} \sigma_f' &= E \cdot 0.623 \cdot \left(\frac{S_u}{E}\right)^{0.832} \\ \varepsilon_f' &= 0.0196 \cdot \varepsilon_f^{0.155} \cdot \left(\frac{S_u}{E}\right)^{-0.53} \end{aligned} \quad (11)$$

where S_u is the ultimate stress and ε_f is the strain to failure at the desired temperature both obtained by tensile tests. Cyclic strength and ductility are determined by this empirical equation system (11) with specific multipliers and exponents calibrated on vast number of tests. Instead the exponents of equation (10) are assumed constant $b = -0.09$ and $c = -0.56$. The ultimate strength S_u is selected for the appropriate temperature and hold time, and it is shown in **Table 3**. Only recently an experimental work on monotonic and low cycle fatigue behaviour of Al2024T3 at room and high temperature has been published (Karakas and Szusta, 2015). A comparison between the adopted modified universal slope method and experimental data is presented in **Figure 5**, showing a good and slightly conservative approximation.

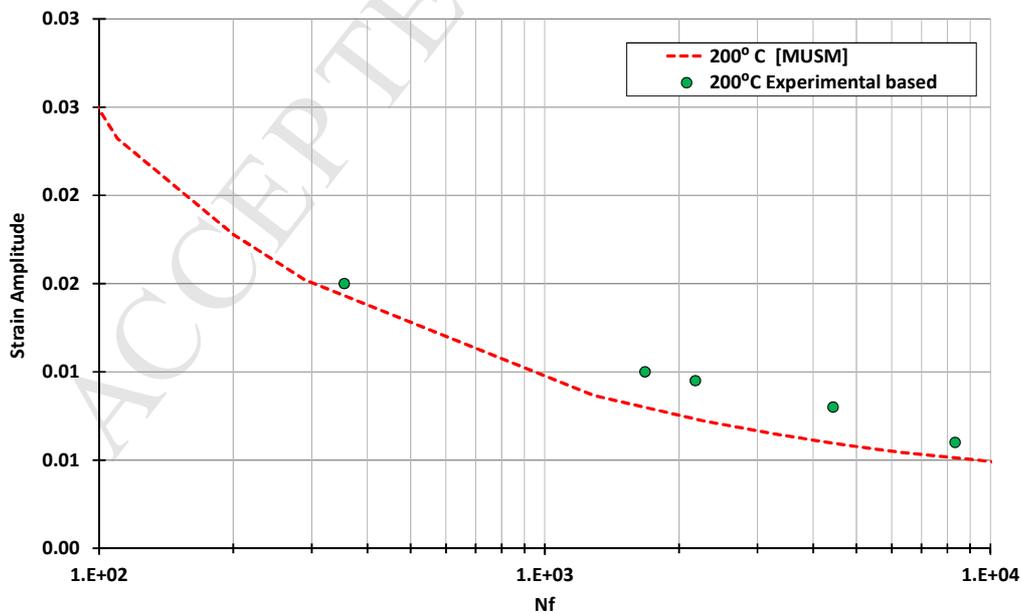


Figure 5 Comparison between Modified Universal Slope Method and experimental results (Karakas and Szusta, 2015).

Table 3 Temperature dependent tensile strength for 2024T3 aluminium alloy.

| S_u [MPa] | 150°C | 175°C | 200°C |
|-------------|-------|-------|-------|
| 0.1 hr | 550 | 436 | 460 |
| 1 hr | 415 | 395 | 370 |
| 100 hrs | 435 | 370 | 305 |
| 1000 hrs | 400 | 330 | 260 |

In order to evaluate the creep rupture time the stress dependent reversed power-law is used:

$$t^* = B \cdot \sigma^{-k} \quad (12)$$

where $B=1.93642E+017$ and $k=6.2252$ are creep rupture material parameters estimated by fitting the experimental creep rupture data available for the required temperature (175°C for the creep-fatigue assessment). When the rupture time is determined the time fraction rule is adopted to calculate the total creep damage. Once both the damages due to fatigue ω_f and creep ω_c are calculated separately, a linear damage interaction $\omega_f + \omega_c \leq 1$ is adopted to calculate the total number of cycle to fail and the total damage as well.

4 Modified strain range partitioning

Strain range partitioning is a method for treating creep-fatigue interaction at elevated temperature where stress multiaxiality is involved. A full description of the strain range partitioning procedure is reported in (Manson and Halford, 1976). Here, as suggested in (Manson and Halford, 1976), further studies have been undertaken in order to understand the effect of anisotropy which arises in composite structures, non-proportional loading and high temperature on the creep-fatigue interaction behaviour. Also, a modification of the method has been proposed aimed at providing information on both the transition and steady-state behaviour. This procedure relies upon the comparison between the ratchetting strain computed between two subsequent hysteresis loops and the ratchetting strain computed within the hysteresis loop itself by using the strain range partitioning approach. A detailed description of the procedure which is based on incremental FEA is reported in the following subsections. Comparison with the LMM procedure is also reported in order to show the capability of the direct methods to provide feasible and computational inexpensive solutions to assess the steady-state cyclic response.

4.1 Evaluation of the equivalent stress and strain

The first step is to compute the strain increments at each time instant within the cycle. We refer to 8 schematic hysteresis loops that, as will be seen in the section 5, characterise the material response under the assigned loading history for both procedures.

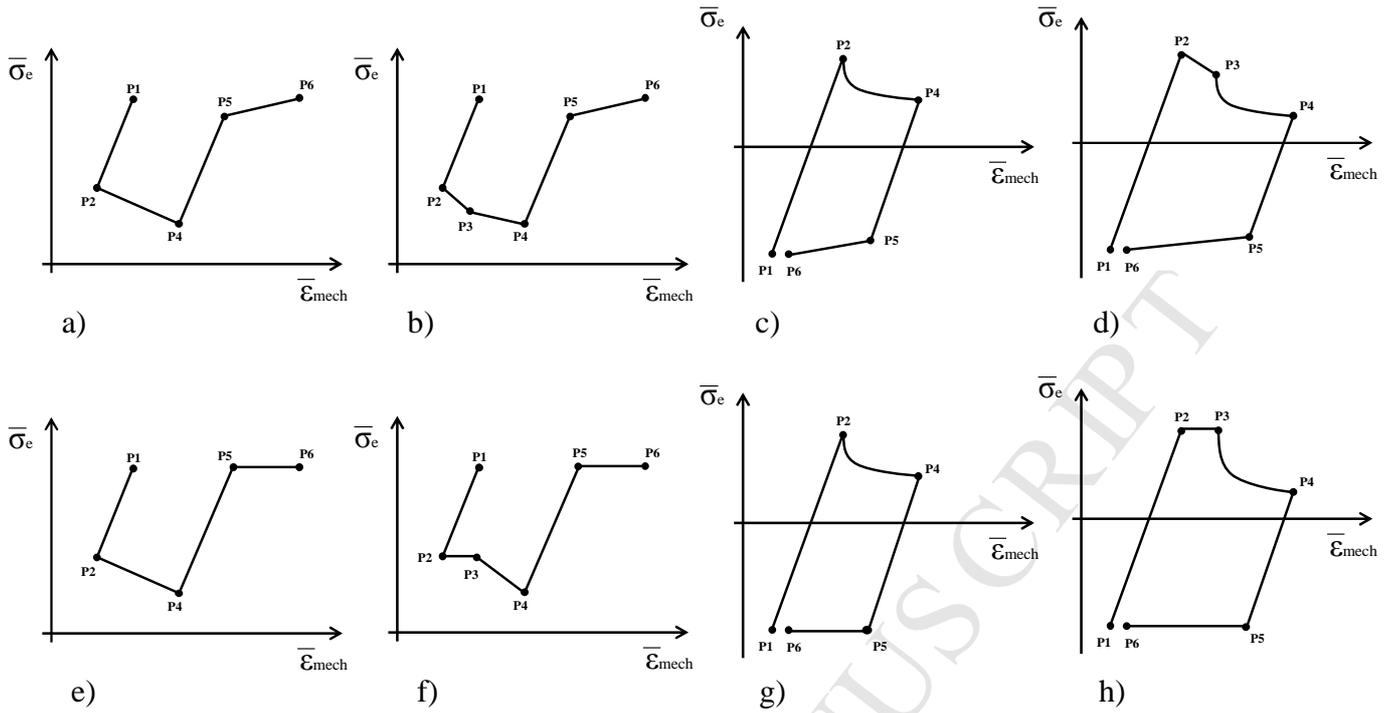


Figure 6 Schematic steady state hysteresis loops for both SBS approach and LMM approach.

Figure 6a-b-c-d show the schematic steady state hysteresis loops related to the step-by-step (SBS) procedure while **Figure 6e-f-g-h** show the hysteresis loops related to the Linear Matching Method (LMM) procedure. The four loops depicted in **Figure 6a-b-e-f** are referred to as total open loops (TOL) whereas the four loops depicted in **Figure 6c-d-g-h** are referred to as reverse open loops (ROL) if the points P1 and P6 are different while for P1=P6 they are referred to as reverse closed loop (RCL). For both procedures the elastic strain increment in loading is computed between points P1-P2, the plastic strain increment in loading between points P2-P3, the creep strain increment between points P3-P4, the elastic strain increment in unloading between points P4-P5, and the plastic strain increment in unloading between points P5-P6. It is noted that point P3 is present in the loops only when plastic strain in loading occurs. Hence for the loops in **Figure 6a-c-e-g** the starting point of the creep phase is P2 and the creep strain increment is computed between points P2-P4.

The main difference between the SBS procedure and the LMM procedure is in computing the load points P2 and P5 within the steady state hysteresis loop when plastic strain occurs in both loading and unloading. Indeed, as the yield stress varies with the temperature (**Table 1**), the yield surface becomes smaller during the loading phase as the temperature increases while during the unloading phase the yield stress increases as the temperature decreases. Thus, the point P2 where the accumulation of plastic strain starts in loading for the loops in **Figure 6b-d** related to the SBS procedure has an equivalent von Mises stress higher than the point P3 where the stress level is equal the yield stress at the peak temperature within the thermal loading history. For the LMM procedure the point P2 depicted in **Figure 6f-h** starts always at the same stress level as P3 which is equal to the yield stress at the peak temperature within the thermal loading history. Same conclusion can be drawn for the point P5 where the accumulation of plastic strain starts in

unloading. As the yield surface increase during the unloading phase for the SBS procedure, point P5 has an equivalent von Mises stress lower than the yield stress at room temperature (**Figure 6b-d**) while for the LMM procedure point P5 depicted in **Figure 6f-h** starts always from the same stress level as P6.

Let's assume that the effect of the three principal components of stress and strain is characterized by single parameters according to the equations:

$$\bar{\sigma}_e = \frac{1}{\sqrt{2}} \sqrt{(\sigma_1 - \sigma_2)^2 + (\sigma_2 - \sigma_3)^2 + (\sigma_3 - \sigma_1)^2} \quad (13)$$

$$\bar{\epsilon}_{el} = \frac{1}{(1+\nu)\sqrt{2}} \sqrt{(\epsilon_1^{el} - \epsilon_2^{el})^2 + (\epsilon_2^{el} - \epsilon_3^{el})^2 + (\epsilon_3^{el} - \epsilon_1^{el})^2} \quad (14)$$

$$\bar{\epsilon}_{in} = \frac{\sqrt{2}}{3} \sqrt{(\epsilon_1^{in} - \epsilon_2^{in})^2 + (\epsilon_2^{in} - \epsilon_3^{in})^2 + (\epsilon_3^{in} - \epsilon_1^{in})^2} \quad (15)$$

wherein $\bar{\sigma}_e$ is the equivalent stress at a generic cycle, time step, and time increment, $\bar{\epsilon}_{el}$ is the equivalent elastic strain and $\bar{\epsilon}_{in}$ is the equivalent strain for the inelastic components where "in" can be "pl" (plastic), or "cr" (creep). For both stress and strain the subscript "1", "2" and "3" stands for maximum principal component, medium principal component and minimum principal component, respectively.

Table 4. Strain increments at different load points of the stabilized hysteresis loop.

| | P1 | P2 | P3 | P4 | P5 | P6 |
|-------------------------------|----------------------------|----------------------------------|----------------------------------|----------------------------------|----------------------------------|----------------------------------|
| Elastic strain | $\bar{\epsilon}_{el_{P1}}$ | $\Delta\bar{\epsilon}_{el_{P2}}$ | $\Delta\bar{\epsilon}_{el_{P3}}$ | $\Delta\bar{\epsilon}_{el_{P4}}$ | $\Delta\bar{\epsilon}_{el_{P5}}$ | $\Delta\bar{\epsilon}_{el_{P6}}$ |
| Plastic strain | n/a | n/a | $\Delta\bar{\epsilon}_{pl_{P3}}$ | n/a | n/a | $\Delta\bar{\epsilon}_{pl_{P6}}$ |
| Creep strain | n/a | n/a | n/a | $\Delta\bar{\epsilon}_{cr_{P4}}$ | n/a | n/a |
| Total inelastic strain | $\bar{\epsilon}_{in_{P1}}$ | n/a | n/a | n/a | n/a | n/a |

Upon defining the effective Young's Modulus as $E_{eff} = \frac{3E}{2(1+\nu)}$ (EDF Energy, 2014) the six load points of the stabilised hysteresis loops by means of the SBS procedure are computed using equation (13), (14), and (15) and the strain increments for each load point within the loop are reported in **Table 4**. It is worth noting that the load point P1 is the last load point of the loop that precedes the stabilized loop. Hence $\bar{\epsilon}_{in_{P1}}$ is the accumulated inelastic strain from the first cycle to the cycle that precedes the stabilized cycle. A similar approach is used by the LMM where all the strain ranges and equivalent stresses are directly calculated for the stabilised hysteresis loop and stored in Abaqus state variables SDV (Abaqus, 2013).

4.2 Evaluation of the algebraic sign of the equivalent stress and strain

As seen in the section 4.1, all the equivalent values are evaluated in magnitude. For practical design situations for which life prediction methods are intended to be used, often involve stresses in more than one direction. Thus, the eventual usage of the strain-range partitioning method requires the entire stabilized stress-strain hysteresis loops to be known. From the values of equivalent stress and strain at each point in the cycle, it then becomes possible to construct an equivalent hysteresis loop wherein at each instant of time the stress is the equivalent stress and the strain is the equivalent strain. However, before this can be done an algebraic sign to indicate tension or compression status must be assigned to both magnitudes of equivalent stress and strain (Manson and Halford, 1976). The method proposed comprises of two stages. The first stage is aimed at evaluating the algebraic sign of the equivalent stress and strain within the first hysteresis loop. In particular, at each instant of time the equivalent stress and strain will be computed according to (13), (14), and (15) but the algebraic sign of $\bar{\sigma}_e$ and $\bar{\epsilon}_{in}$ will be the same as the one of the dominant stress component i.e. the sign of the largest component between σ_1 and σ_3 for the stress and the sign of the largest component between ϵ_1^{in} and ϵ_3^{in} for the strain. **Table 5** shows the sign of the first cycle related to the reference transition hysteresis loops depicted in **Figure 7**. The circular, elliptical and square cross sections are referred to as C11, C21, and S11 respectively within **Table 5** where M0 stands for mechanical load $\sigma_p = 0$, M025 stands for $\sigma_p = 0.25 \times \sigma_y^{(25)}$, and M05 stands for $\sigma_p = 0.5 \times \sigma_y^{(25)}$. As previously mentioned, D1 stands for 1 hour of dwell time and D100 stands for 100 hours of dwell period. Also, L, C, and U stand for end of loading phase, end of creep phase, and end of unloading phase respectively.

Table 5. Sign of von Mises stresses at the first cycle for the reference transition hysteresis loops in Figure 7.

| | | $\bar{\sigma}_e$ | σ_1 | σ_3 | Sign |
|---------------|---|------------------|------------|------------|------|
| C11-M0-D1 | L | 322 | 56.0598 | -313.566 | - |
| | C | 254.933 | 46.2544 | -249.238 | - |
| | U | 92.2509 | 78.5282 | -27.7436 | + |
| C11-M025-D100 | L | 322 | 159.936 | -183.87 | - |
| | C | 179.248 | 128.372 | -63.2164 | + |
| | U | 312.495 | 300.479 | -40.3999 | + |
| C11-M05-D100 | L | 322 | 261.845 | -78.3248 | + |
| | C | 250.321 | 264.915 | -22.5227 | + |
| | U | 371 | 361.761 | -16.3537 | + |
| C21-M0-D100 | L | 322 | 232.372 | -106.614 | + |
| | C | 165.525 | 180.501 | -2.45734 | + |
| | U | 371 | 163.554 | -228.67 | - |

| | | | | | |
|---------------|---|---------|---------|----------|---|
| C21-M025-D100 | L | 322 | 145.467 | -209.131 | - |
| | C | 149.572 | 88.3183 | -70.7236 | + |
| | U | 328.142 | 265.309 | -74.3077 | + |
| C21-M05-D100 | L | 322 | 191.087 | -156.857 | + |
| | C | 222.665 | 197.843 | -51.489 | + |
| | U | 371 | 293.351 | -134.602 | + |
| S11-M0-D100 | L | 322 | 365.054 | -2.42783 | + |
| | C | 188.02 | 278.731 | 61.8641 | + |
| | U | 371 | 168.92 | -232.541 | - |

With regards to the second stage, it is aimed at evaluating the sign of the hysteresis loop from the second cycle to the stabilised cycle. Uppermost, we compute the ratchetting strain per cycle in three steps:

1. At the end of each load cycle, 6 components of the mechanical strain are obtained by subtracting corresponding thermal strain components from total strain components. And then 6 components of the ratchetting strain are calculated for each load cycle by the difference in corresponding components of mechanical strain between the end and the beginning of each load cycle;
2. The equivalent ratchetting strain for each load cycle from the 2nd cycle to the stabilized cycle can then be calculated by equation (15) since ratchetting strain is treated as inelastic strain;
3. Taking into account only the final steady state cycle, we compare the equivalent ratchetting strain $\Delta\bar{\epsilon}_{rcht}$ with the equivalent plastic strain increment in loading $\Delta\bar{\epsilon}_{pl_{P3}}$, the equivalent creep strain $\Delta\bar{\epsilon}_{cr_{P4}}$ and the equivalent plastic strain increment in unloading $\Delta\bar{\epsilon}_{pl_{P6}}$. Three scenarios can occur:

$$\Delta\bar{\epsilon}_{rcht} \cong \Delta\bar{\epsilon}_{rcht}^{summ} = \Delta\bar{\epsilon}_{pl_{P3}} + \Delta\bar{\epsilon}_{cr_{P4}} + \Delta\bar{\epsilon}_{pl_{P6}} \rightarrow \text{total open loop (TOL)} \quad (16)$$

$$\Delta\bar{\epsilon}_{rcht} \cong \Delta\bar{\epsilon}_{rcht}^{diff} = \Delta\bar{\epsilon}_{pl_{P3}} + \Delta\bar{\epsilon}_{cr_{P4}} - \Delta\bar{\epsilon}_{pl_{P6}} \rightarrow \text{reverse open loop (ROL)} \quad (17)$$

$$\Delta\bar{\epsilon}_{rcht} \cong 0 \rightarrow \Delta\bar{\epsilon}_{pl_{P3}} + \Delta\bar{\epsilon}_{cr_{P4}} \cong \Delta\bar{\epsilon}_{pl_{P6}} \rightarrow \text{reverse closed loop (RCL)} \quad (18)$$

Upon comparing the ratchetting strain, we can use equations (16) and (17), to evaluate the percentage error as:

$$err\%_{sum} = \frac{|\Delta\bar{\epsilon}_{rich} - \Delta\bar{\epsilon}_{rich}^{summ}|}{\Delta\bar{\epsilon}_{rich}} \times 100 \quad (19)$$

$$err\%_{diff} = \frac{|\Delta\bar{\epsilon}_{rich} - \Delta\bar{\epsilon}_{rich}^{diff}|}{\Delta\bar{\epsilon}_{rich}} \times 100 \quad (20)$$

By computing the percentage error from equations (19) and (20), the stabilised hysteresis loops can be drawn and the 6 load points (5 if no plastic strain in loading occurs i.e. there is no point P3) are univocally determined in terms of both magnitude and sign. Indeed a total open loop (TOL) is considered if $err\%_{sum} < err\%_{diff}$ instead a reverse open loop (ROL) is considered if $err\%_{sum} > err\%_{diff}$. It is worth pointing out that a TOL in this paper is a hysteresis loop where the von Mises stress at each load point is always positive as shown in **Figure 6a-b-e-f**. Instead, a ROL can have either the stresses of both the loading and creep phase positive and the stresses of the unloading phase negative as shown in **Figure 6c-d-g-h** or vice versa.

5 Application of the concepts to MMCs and discussions

5.1 Transition behaviour

As discussed in section 4, we proposed a variation of the strain range partitioning in order to evaluate both the transition behaviour and the steady state behaviour of long fibre MMCs.

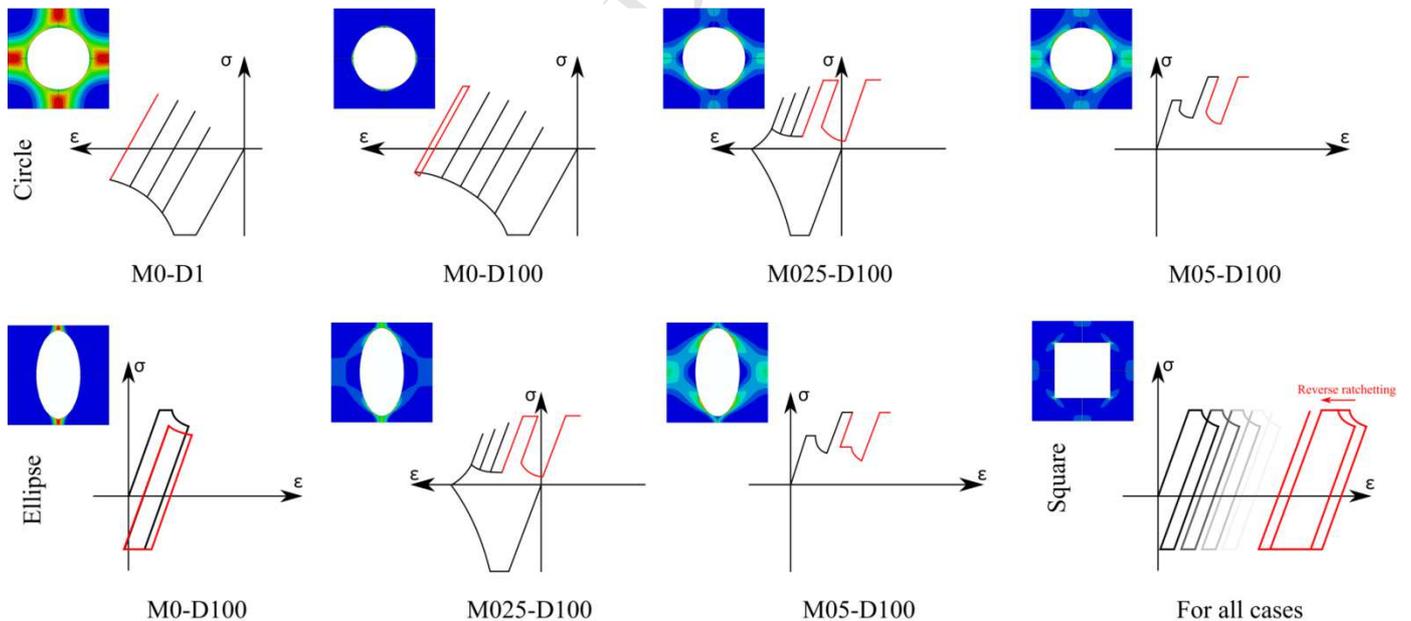


Figure 7 Schematic transition hysteresis loops for the 3 cross-section studied under the load history in Figure 4b for different mechanical loads and different dwell times, where the steady state loop is highlighted in RED.

Further explanations on the latter behaviour will be provided in subsection 5.2. Here, a physical explanation of the transition behaviour that justifies the method adopted is discussed. Detailed results are only presented for the steady state behaviour whereas the transition behaviour is discussed in a schematic way. This methodology can be applied to different integration points within the structures in order to find the most critical location to assess. Here, for all the geometries considered, the integration point chosen is the one with the highest creep damage.

Figure 7 shows the schematic transition behaviour for the 3 cross-sections studied for different mechanical loads and dwell times. Contours of the creep strain increment at the stabilised cycle $\Delta\bar{\epsilon}_{crP4}$ show the area where the highest creep damage occurs. As discussed in section 3, the load points investigated experience shakedown for both the circular cross-section and the elliptical cross-section if no creep dwell is introduced. Instead reverse plasticity behaviour is expected for the square cross-section. By introducing a creep dwell within the cyclic thermal loading at the tensile peak, different scenarios arise as reported in (Barbera et al., 2016b) for metallic structures at elevated temperature. Here a new mechanism is seen when the off-axis constant mechanical load in **Figure 4-b**, is applied. Indeed, for small creep dwell e.g. D1 and no mechanical load M0, the composite with the circular cross-section remains in shakedown while for D100 it experiences a reverse closed loop (RCL). These two material responses have already been discussed in (Barbera et al., 2016b). By increasing the mechanical load e.g. M025, there is a sign variation that leads the structures to experience creep-ratchetting with a total open loop (TOL). This is because the thermal load and the mechanical load act in the opposite direction so that the more the thermal stress relaxes the more the mechanical load becomes predominant. For the highest mechanical load applied, M05, the equivalent stress is positive in loading because the mechanical load is predominant from the first cycle. With regards to the elliptical cross-section, for M0 and all the dwell times, a steady state reverse closed loop response is seen after a transition phase where a sequence of reverse loops show creep-ratchetting. Compared to the circular cross-section, the reverse closed loops of the elliptical cross-section have the stresses of the loading and creep phases positive from the first cycle (**Table 5**) to the stabilised one. This is mainly due to the positive value of the stress component along the y direction as it affects the magnitude of the maximum principal component σ_1 such that it becomes predominant during the loading compared to the minimum principal component σ_3 . Instead for the circular cross-section the magnitude of the minimum principal component σ_3 is affected by the stress component along the fibre direction z. Therefore the magnitude of σ_3 is higher than σ_1 during loading and lower than σ_1 during unloading. Regarding the square cross-section the creep dwell leads the structure to experience negative reverse ratchetting after a transition phase where the structure experiences positive ratchetting with a reverse open loop. This because the stress relaxation enhances the plastic strain in unloading which after a certain number of cycles is not more compensated by the inelastic strain in loading.

5.2 Steady-state behaviour

The steady-state cyclic stress-strain hysteresis loops for the three geometries studied are presented. Full inelastic step-by-step simulations have been used to verify the LMM results. Modified strain range partitioning, described in section 4, has been used. All the strain increments, ratchetting strains per cycles, and percentage errors are reported in tabular form in order to facilitate the understanding of the method adopted.

Table 6. Circular cross-section stress and strain ranges for the stabilised hysteresis loops for D100.

| | $\bar{\sigma}_{e_{P3}}$ | $\bar{\sigma}_{e_{P4}}$ | $\bar{\sigma}_{e_{P6}}$ | $\Delta\bar{\epsilon}_{pl_{P3}}$ | $\Delta\bar{\epsilon}_{cr_{P4}}$ | $\Delta\bar{\epsilon}_{pl_{P6}}$ | $\Delta\bar{\epsilon}_{rtch}$ | |
|-----|-------------------------|-------------------------|-------------------------|----------------------------------|----------------------------------|----------------------------------|-------------------------------|------|
| LMM | 52.4787 | 50.858 | 371 | 0.00E+00 | 2.60E-05 | 2.30E-05 | 3.00E-6 | M0 |
| SBS | 46.089 | 45.074 | 371 | 0.00E+00 | 1.71E-05 | 1.79E-05 | 8.00E-7 | |
| LMM | 138.516 | 134.053 | 371 | 0.00E+00 | 6.38E-04 | 1.78E-04 | 6.84E-04 | M025 |
| SBS | 138.694 | 133.922 | 371 | 0.00E+00 | 6.32E-04 | 1.82E-04 | 6.73E-04 | |
| LMM | 291.982 | 252.392 | 371 | 0.00E+00 | 6.17E-03 | 1.83E-03 | 7.35E-03 | M05 |
| SBS | 296.096 | 249.94 | 371 | 0.00E+00 | 5.88E-03 | 2.18E-03 | 7.14E-03 | |

Table 7. Circular cross-section's percentage error for the stabilised hysteresis loops for D100.

| | $\Delta\bar{\epsilon}_{rtch}$ | $\Delta\bar{\epsilon}_{rtch}^{summ}$ | $\Delta\bar{\epsilon}_{rtch}^{diff}$ | $err\%_{sum}$ | $err\%_{diff}$ | M | Loop |
|-----|-------------------------------|--------------------------------------|--------------------------------------|---------------|----------------|------|------|
| LMM | 3.00E-6 | 4.90E-05 | 3.00E-06 | 1533.33% | 0.00% | M0 | RCL |
| SBS | 8.00E-7 | 3.50E-05 | 8.00E-07 | 4275.00% | 0.00% | | RCL |
| LMM | 6.84E-04 | 8.16E-04 | 4.60E-04 | 19.30% | 32.75% | M025 | TOL |
| SBS | 6.73E-04 | 8.14E-04 | 4.50E-04 | 20.95% | 33.14% | | TOL |
| LMM | 7.35E-03 | 8.00E-03 | 4.34E-03 | 6.24% | 42.36% | M05 | TOL |
| SBS | 7.14E-03 | 8.06E-03 | 3.70E-03 | 12.89% | 48.18% | | TOL |

Table 6 reports for the circular cross-section the stress and strain ranges computed by the LMM and SBS for the three different load points A1, A2, and A3 in **Figure 4-a** and for a dwell time of 100 hours. Comparing the results of both approaches, it can be seen that the LMM overestimates the plastic strain range in unloading $\Delta\bar{\epsilon}_{pl_{P6}}$ and the creep strain range $\Delta\bar{\epsilon}_{cr_{P4}}$ for M0. Instead for M025 and M05 the highest percentage error is lower than 16%. The correlation between the ratchetting percentage errors and the type of hysteresis loop for the circular cross-section is shown in **Table 7**. All the data are computing according to the equations (16), (17), (18), (19) and (20). What can be clearly seen in **Table 7** is that for M0, a closed reverse loop is considered as $\Delta\bar{\epsilon}_{rtch} \cong 0$. When the mechanical load increases e.g. M025 or M05, a total open loop is seen as $err\%_{diff}$ is higher than $err\%_{sum}$.

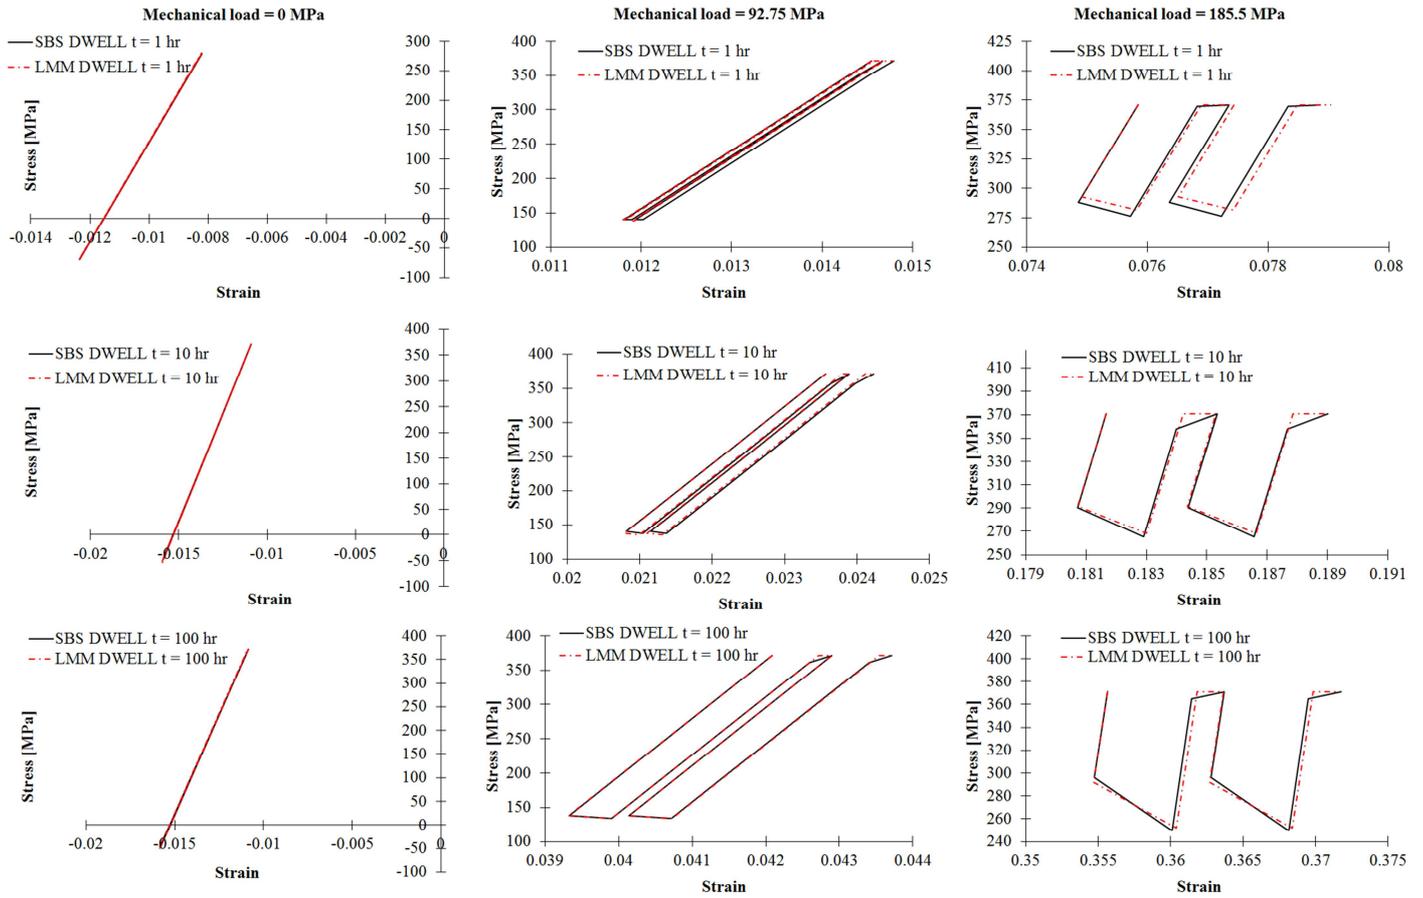


Figure 8 Steady-state hysteresis loops for the circular cross-section for three dwell times (1hr, 10hrs, 100hrs) and three mechanical load ($\sigma_p = 0$, $\sigma_p = 0.25 \times \sigma_y^{(25)}$, $\sigma_p = 0.5 \times \sigma_y^{(25)}$).

Figure 8 shows all the stabilised hysteresis loops for the circular cross-section for all the load scenarios investigated. As we have seen in **Figure 7** with regard to the circular cross-section, when the mechanical load is equal zero, there is no sign variation during the stress relaxation and the structure exhibits either shakedown for small dwell times i.e. D1 or reverse plasticity for longer dwell time i.e. D10 and D100. When the off-axis mechanical load is applied the stabilised loop is a total open and creep-ratcheting occurs.

Table 8. Elliptical cross-section stress and strain ranges for the stabilised hysteresis loops for D100.

| | $\bar{\sigma}_{e_{P3}}$ | $\bar{\sigma}_{e_{P4}}$ | $\bar{\sigma}_{e_{P6}}$ | $\Delta \bar{\epsilon}_{pl_{P3}}$ | $\Delta \bar{\epsilon}_{cr_{P4}}$ | $\Delta \bar{\epsilon}_{pl_{P6}}$ | $\Delta \bar{\epsilon}_{rtch}$ | |
|-----|-------------------------|-------------------------|-------------------------|-----------------------------------|-----------------------------------|-----------------------------------|--------------------------------|------|
| LMM | 226.949 | 142.733 | 371 | 0.00E+00 | 1.54E-03 | 1.56E-03 | 2.00E-5 | M0 |
| SBS | 228.033 | 141.01 | 371 | 0.00E+00 | 1.56E-03 | 1.55E-03 | 1.00E-5 | |
| LMM | 243.826 | 176.375 | 371 | 0.00E+00 | 2.50E-03 | 3.01E-03 | 4.66E-03 | M025 |
| SBS | 247.21 | 170.436 | 371 | 0.00E+00 | 2.32E-03 | 3.46E-03 | 4.61E-03 | |
| LMM | 322.127 | 267.454 | 371 | 1.14E-03 | 7.95E-03 | 4.76E-02 | 5.54E-02 | M05 |
| SBS | 322 | 256.712 | 371 | 1.25E-03 | 6.21E-03 | 5.00E-02 | 5.33E-02 | |

Table 9. Elliptical cross-section's percentage error for the stabilised hysteresis loops for D100.

| | $\Delta \bar{\epsilon}_{rtch}$ | $\Delta \bar{\epsilon}_{rtch}^{summ}$ | $\Delta \bar{\epsilon}_{rtch}^{diff}$ | $err\%_{sum}$ | $err\%_{diff}$ | M | Loop |
|-----|--------------------------------|---------------------------------------|---------------------------------------|---------------|----------------|------|------|
| LMM | 2.00E-5 | 3.10E-03 | 2.00E-5 | 154000.00% | 0.00% | M0 | RCL |
| SBS | 1.00E-5 | 3.11E-03 | 1.00E-5 | 31000.00% | 0.00% | | RCL |
| LMM | 4.66E-03 | 5.51E-03 | 5.10E-04 | 18.24% | 89.06% | M025 | TOL |
| SBS | 4.61E-03 | 5.78E-03 | 1.14E-03 | 25.38% | 75.27% | | TOL |
| LMM | 5.54E-02 | 5.67E-03 | 3.85E-02 | 2.33% | 30.49% | M05 | TOL |
| SBS | 5.33E-02 | 5.75E-03 | 4.25E-02 | 7.80% | 20.19% | | TOL |

Table 8 compares the stress and strain ranges between LMM and SBS with regards to the elliptical cross-section at D100. Here the LMM overestimates the creep strain range when the mechanical load is M05. For all the other ranges the percentage error is lower than 13%. **Table 9**, provides the intercorrelations between the percentage errors and the type of hysteresis loop for the elliptical cross-section. As previously discussed for the circular cross-section, when the mechanical load is equal to zero, a closed reverse loop is considered. Instead, creep-ratchetting is seen in the form of total open loop for M025 and M05.

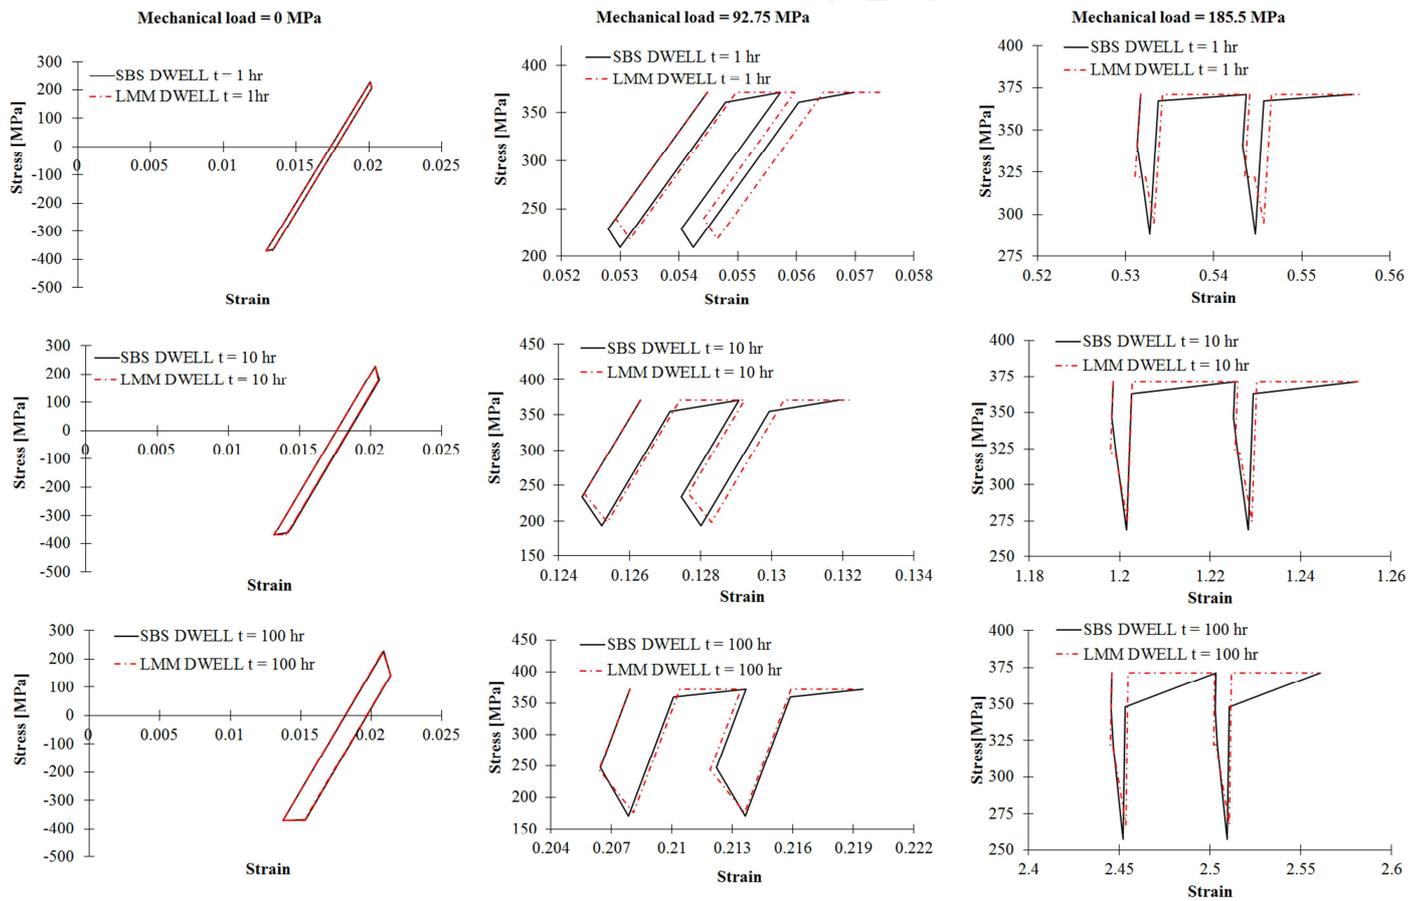


Figure 9 Steady-state hysteresis loops for the elliptical cross-section for three dwell times (1hr, 10hrs, 100hrs) and three mechanical load ($\sigma_p = 0$, $\sigma_p = 0.25 \times \sigma_y^{(25)}$, $\sigma_p = 0.5 \times \sigma_y^{(25)}$).

With regard to the stabilised hysteresis loops for the elliptical cross-section shown in **Figure 9** for all the dwell times investigated the structure's response is in agreement with the results provided in **Table 9**. For M05, the main difference between the elliptical cross-section and the circular cross-section is that the open loops for the former accumulate plastic strain in loading and unloading. This leads the structure to experience a higher ratchetting strain per cycle compared to the scenario with M025.

Table 10. Square cross-section stress and strain ranges for the stabilised hysteresis loops for D100.

| | $\bar{\sigma}_{e_{P3}}$ | $\bar{\sigma}_{e_{P4}}$ | $\bar{\sigma}_{e_{P6}}$ | $\Delta\bar{\epsilon}_{pl_{P3}}$ | $\Delta\bar{\epsilon}_{cr_{P4}}$ | $\Delta\bar{\epsilon}_{pl_{P6}}$ | $\Delta\bar{\epsilon}_{rtch}$ | |
|-----|-------------------------|-------------------------|-------------------------|----------------------------------|----------------------------------|----------------------------------|-------------------------------|------|
| LMM | 322 | 185.855 | 371 | 2.51E-03 | 4.17E-03 | 6.91E-03 | 2.71E-04 | M0 |
| SBS | 322 | 183.691 | 371 | 2.51E-03 | 4.06E-03 | 6.83E-03 | 3.00E-04 | |
| LMM | 322 | 185.443 | 371 | 2.52E-03 | 4.06E-03 | 7.15E-03 | 5.47E-04 | M025 |
| SBS | 322 | 184.072 | 371 | 2.47E-03 | 4.06E-03 | 7.09E-03 | 5.02E-04 | |
| LMM | 322 | 198.515 | 371 | 2.97E-03 | 4.69E-03 | 1.00E-02 | 2.69E-03 | M05 |
| SBS | 322 | 210.653 | 371 | 3.01E-03 | 4.66E-03 | 1.01E-02 | 2.65E-03 | |

Table 11. Square cross-section's percentage error for the stabilised hysteresis loops for D100.

| | $\Delta\bar{\epsilon}_{rtch}$ | $\Delta\bar{\epsilon}_{rtch}^{summ}$ | $\Delta\bar{\epsilon}_{rtch}^{diff}$ | $err\%_{sum}$ | $err\%_{diff}$ | M | Loop |
|-----|-------------------------------|--------------------------------------|--------------------------------------|---------------|----------------|------|------|
| LMM | 2.71E-04 | 1.36E-02 | 2.30E-04 | 4914.76% | 15.13% | M0 | ROL |
| SBS | 3.00E-04 | 1.34E-02 | 2.60E-04 | 4366.67% | 13.33% | | ROL |
| LMM | 5.47E-04 | 1.37E-02 | 5.70E-04 | 2410.05% | 4.20% | M025 | ROL |
| SBS | 5.02E-04 | 1.36E-02 | 5.60E-04 | 2613.15% | 11.55% | | ROL |
| LMM | 2.69E-03 | 1.77E-02 | 2.34E-04 | 556.51% | 13.01% | M05 | ROL |
| SBS | 2.65E-03 | 1.78E-02 | 2.43E-04 | 570.57% | 8.30% | | ROL |

Table 10 reports the stress and strain ranges at D100 for the square cross-section for the three load scenarios considered. Here the comparison between LMM and SBS shows a percentage error for all the strain ranges lower than 3%. **Table 11** shows the same information as the previous cross-sections investigated reported in **Table 7** and **Table 9**. Here reverse open loops are considered for all the load scenarios as $err\%_{diff}$ is always lower than $err\%_{sum}$.

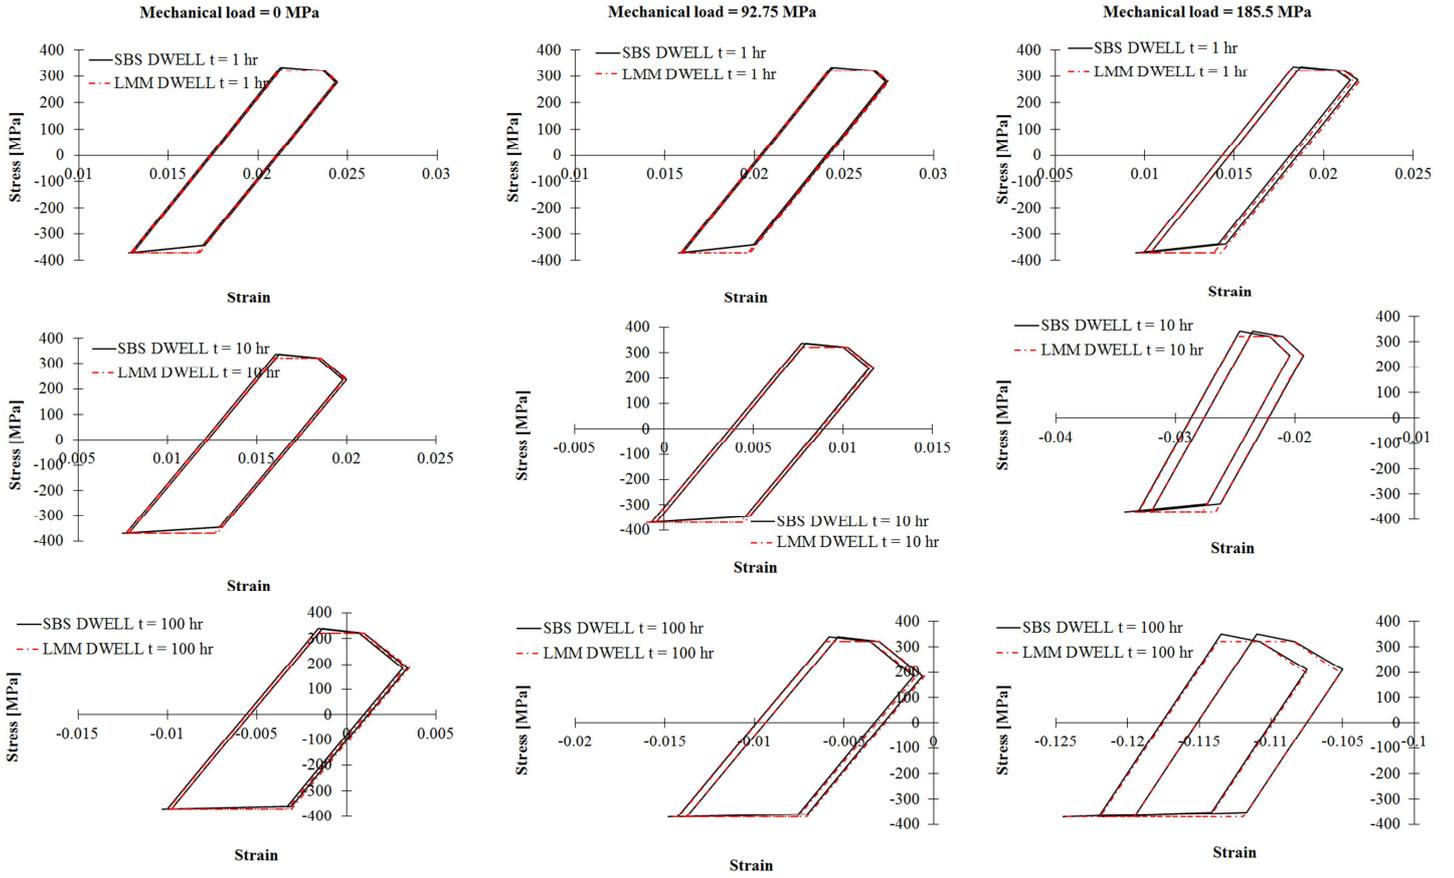


Figure 10 Steady-state hysteresis loops for the square cross-section for three dwell times (1hr, 10hrs, 100hrs) and three mechanical load ($\sigma_p = 0$, $\sigma_p = 0.25 \times \sigma_y^{(25)}$, $\sigma_p = 0.5 \times \sigma_y^{(25)}$).

Figure 10 shows the stabilised hysteresis loops for the square cross-section for all the mechanical loads and dwell times. As we have seen in **Figure 7** the square cross-section shows a reverse ratchetting at the stabilised loop after a certain number of cycles during the transition phase. This is because during the transition phase the sum of the plastic strain in loading $\Delta \varepsilon_{pl}^L$ and the creep strain $\Delta \varepsilon_{cr}$ is higher than the plastic strain in unloading $\Delta \varepsilon_{pl}^U$. Therefore the loop moves rightward until $\Delta \varepsilon_{pl}^U$ is lower than the aforementioned sum. When $\Delta \varepsilon_{pl}^U$ becomes dominant the steady-state cycle moves leftward. From **Figure 10** it is clear that the higher the dwell time the sooner the transition from the rightward ratchetting to a leftward ratchetting is reached.

6 Creep fatigue and creep ratchetting assessment

The assessment of the microstructures has been done by considering the effect of the steady-state on the crack initiation process. As depicted in **Figure 7**, by changing the applied load and fibre geometry the steady-state response can change remarkably. The scope of this section is to understand and provide more information on how these responses could trigger crack initiation within the metal matrix. It worth noting that the matrix and the fibre are considered perfectly bonded.

6.1 Cyclic thermal load without transverse mechanical load

When no mechanical load is applied, only the thermal stress caused by the coefficient of thermal expansion mismatch is present. For this condition, the best geometry is the circular one, as the response is strict shakedown for small dwell times i.e. D1 and closed loop for longer dwell times i.e. D10 and D100 as shown in **Figure 8**. For the ellipse and the square section, a closed reverse loop response has been observed for all the dwell times investigated as shown in **Figure 9** and **Figure 10**. In both cases the creep-fatigue interaction lead to the initiation of a crack within the matrix and it is driven by the creep damage. In both the geometries, the thermal stresses are subjected to a large stress relaxation as shown in **Figure 11a**. The stress relaxation is responsible for the creep damage accumulated during each creep dwell. The trend of the stress relaxation is very similar but the stress at the start of the creep dwell is much higher for the square fibre. In turn, as depicted in **Figure 11b**, the creep strain accumulated during the increasing creep dwell is larger for the square geometry. This is caused by the higher stress occurring during the creep dwell. The large creep strain accumulation and stress relaxation exhibited by the square fibre is the main cause of reversed creep ratchetting shown in **Figure 7**. However, this ratchet strain per cycle is small and compressive preventing any fracture due to excessive deformation.

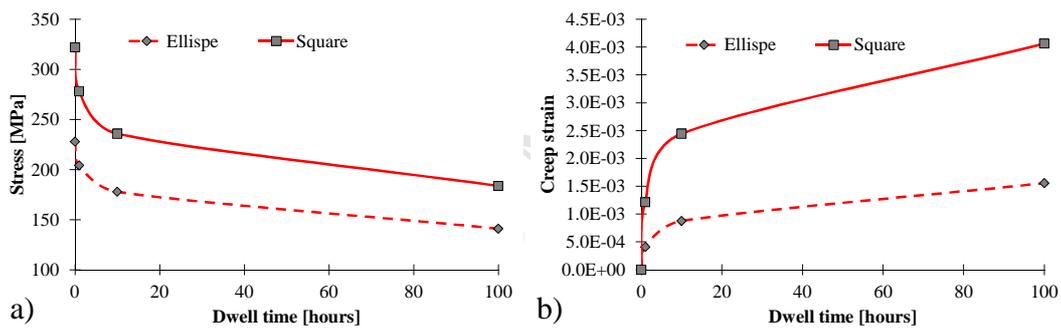


Figure 11 a) Stress relaxation and b) creep strain accumulation during increasing creep dwell.

In terms of overall creep fatigue life, which in both cases is dominated by the creep damage, the ellipse performs generally better than the square fibre as reported in **Figure 12**. This is due to the higher stress at the start of the creep dwell of the square fibre, which is 322 MPa against the 226 MPa of the elliptic fibre. For increasing dwell time the endurance predicted for both the geometries reduce significantly. The decrease in creep-fatigue life is nearly linear for the geometries investigated suggesting that both are affected in a similar way by the creep dwell length.

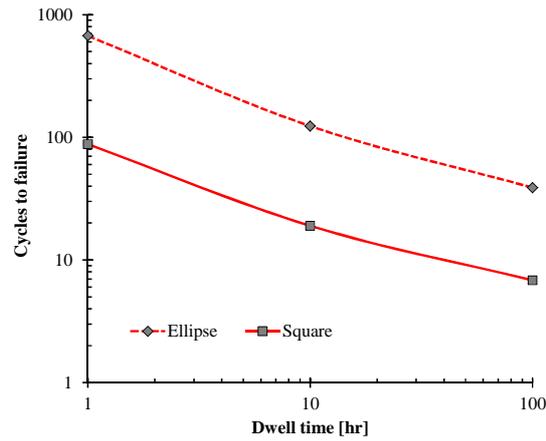


Figure 12 Creep-fatigue endurance for the ellipse and circle fibres without mechanical load.

The failure mechanism associated to the cyclic thermal load for a creep dwell of 100 hours is depicted in **Figure 13** for both cases. The ellipse has expected life of 36 cycles and the area where the damage initiate is shown in **Figure 13a**. The blue area is relatively large and spread on both fibre sides along the vertical axis. Commonly creep-fatigue failure mechanism is considered a localized mechanism associated to the initiation of a crack, as it is for the square (**Figure 13b**). However, for the elliptical cross section a remarkable volume of material is expected to fail. This can be explained by considering the effect of the fibre geometry, which enhances the geometrical constraint between each fibre. Conversely, for the square the failure mechanism is localized at the inner edge of the square fibre, where the stresses are at the highest point. This causes a significant reduction in creep-fatigue life, which for the case considered is only 3 cycles.

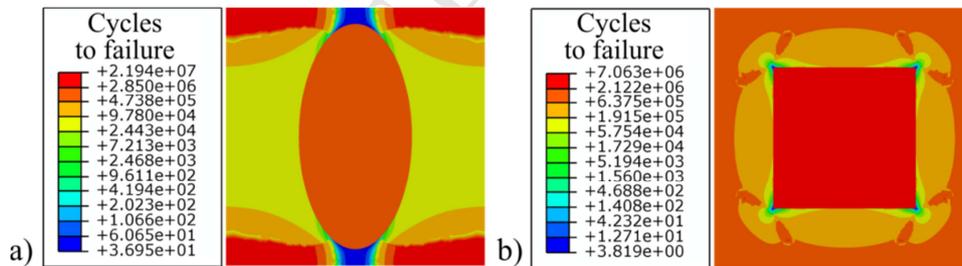


Figure 13 Creep-fatigue life of the a) ellipse and b) square fibre subjected to a cyclic thermal load and a creep dwell of 100 hours.

6.2 Cyclic thermal load with a transverse mechanical load

When a mechanical load is applied, all the geometries analysed tend to exhibit creep ratchetting, which competes with creep-fatigue crack initiation. The increase of dwell time enhances the creep and fatigue damage in all the geometries. Also, creep-ratchetting is affected by the dwell time considered and the magnitude of inelastic strain accumulated at each cycle also increases with the mechanical load. When a constant transverse mechanical of 92.75 MPa is applied, creep-fatigue interaction and creep-ratchetting compete. For circular and elliptical cross-section, **Figure 14a-b**, creep-fatigue interaction is dominant up to a threshold. This threshold is dependent on the cross-section and is around 30

hours and 10 hours for the circular and elliptical cross-section respectively. Creep-ratchetting becomes a significant failure mechanism only for long dwells, leading to a high-temperature fracture within the matrix. Conversely for the square cross-section, as it is shown in **Figure 14c**, creep-fatigue interaction is always dominant.

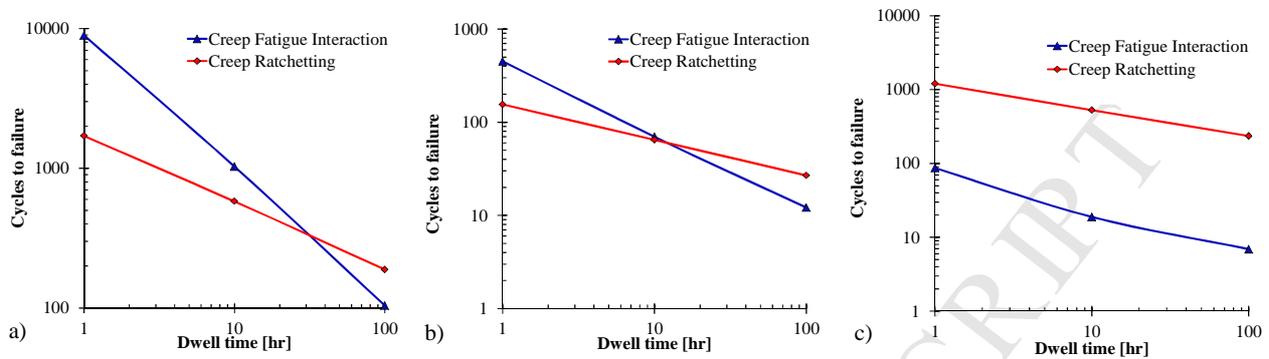


Figure 14 Creep-fatigue and creep ratchetting endurance for the a) circular, b) elliptical and c) square geometries subjected to cyclic temperature of 175 °C and a constant mechanical load of 92.75 MPa with an increasing dwell time.

The cyclic stress response obtained for the three geometries at each loading step is reported in **Figure 15**, where the von Mises stress contours for a cyclic temperature of 175 °C and a constant mechanical load of 92.75 MPa are shown. The stress distribution at each loading step is dramatically affected by the fibre's shape. During the loading, phase increasing stress levels can be observed, the highest is obtained by the square fibre. The subsequent creep dwell induces a stress relaxation, which leads to partial stress redistribution. This is evident for the elliptical cross-section, which shows a clear change of the most stressed location. Conversely for the circular fibre, stress relaxation is marginal and no significant stress redistribution occurs. In the square fibre, the large residual stresses generated by cyclic plasticity leads to a large stress relaxation and redistribution. During the unloading phase, all the geometries respond in a similar way reaching the yield in a large area of the matrix.

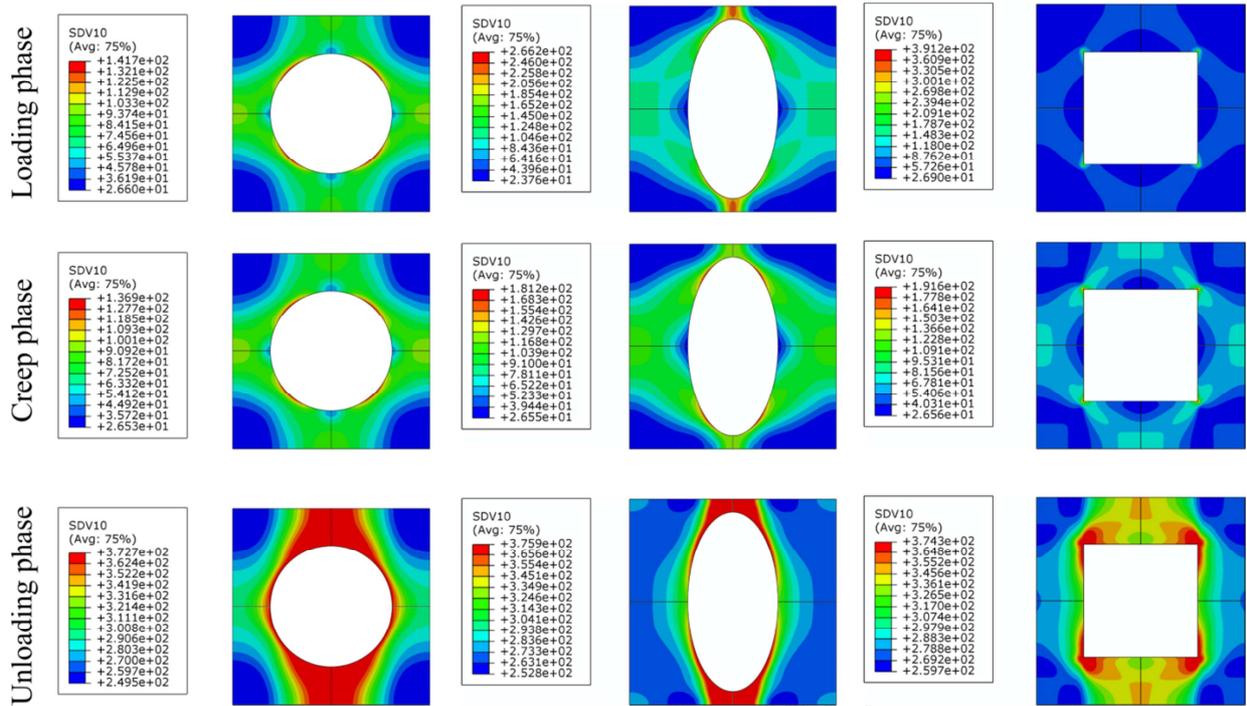


Figure 15 von Mises stress for circular, elliptical and square cross-sections subjected to cyclic temperature of $175\text{ }^{\circ}\text{C}$ and a constant mechanical load of 92.75 MPa with 100 hours of creep dwell time.

By considering the results obtained and shown in **Figure 15** and the cyclic responses reported in **Figure 8**, **Figure 9** and **Figure 10** it is clear that the failure mechanisms are profoundly affected by a series of crucial parameters. These crucial parameters are the stress at the start of the creep dwell, which mainly affects the creep damage and the total strain range that affect the fatigue damage. The stress at the start of the creep dwell has been found to be always tensile and relatively high. The highest stress of 322 MPa has been identified in the square fibre and the lowest of 132 MPa in the circular fibre. For all the cases studied creep damage has consistently been found to be more damaging than fatigue damage, which is never dominant except for very short dwells.

7 Conclusions

In this work, the LMM and eDSCA numerical method has been used to study the effect of the fibre cross-section on the microstructural cyclic response of MMCs at high-temperature. The numerical results have been also extensively validated by using inelastic step-by-step finite element analysis. The cyclic response for all the cross-sections has been identified for three representative dwell times and three mechanical loads. The effects of the fibre cross-section geometries, off-axis mechanical load and dwell time duration have been studied. The results obtained have been discussed pointing out their implications on the microstructural cyclic response, also defining basic rules to construct the proper stabilised hysteresis loop. These rules have been crucial for an accurate assessment of the microstructural integrity for different loading conditions. The main results obtained within this research work are as follow:

1. A modification of the existing strain range partitioning procedure for the treatment of multiaxial creep-fatigue and for the construction of the cyclic hysteresis loop has been proposed. A detailed methodology to evaluate

the sign of von Mises stress, at the stabilised hysteresis loop, has been reported. It relies upon the comparison between the ratchetting strains reported in equations (16) and (17).

2. Transitional behaviour of the hysteresis loops has been carefully identified and discussed. This has been found to be mainly affected by the local thermomechanical stress. Furthermore, the final response of the stabilised hysteresis loop is drastically influenced by the magnitude of the mechanical load. When this dominates over thermal load, creep ratchetting is observed.
3. In terms of structural integrity, as expected, the circular cross-section is the most reliable. However, when primary load is applied, creep-ratchetting is always present. For the circular and elliptical cross-sections ratchetting becomes dominant by a precise threshold. Conversely, creep-fatigue interaction is dominant for the square cross-section.
4. For all the geometries and load conditions examined the most critical damage mechanism is the high-temperature creep, which dominates over the fatigue damage. This is enhanced mainly by the high level of stress at the start of the creep dwell. The introduction of a creep dwell poses severe limitations to the material endurance that needs to be accounted during the design process.
5. Both shape of the fibre cross-section and fibre arrangement can be detrimental regarding the creep-fatigue life by enhancing the geometrical constraint. This has been identified for the elliptical cross-section, where the creep-fatigue crack initiation tends to initiate in a larger area compared to the other two geometries.

The results obtained further extended the knowledge of the creep-fatigue interaction response of MMCs subjected to cyclic load at high-temperature. The information obtained forms the basis necessary to construct a macro-scale model for creep-fatigue response, which is currently unavailable. Furthermore, this work further demonstrates the capabilities of direct methods, such as the LMM, in assessing complex microstructures.

Acknowledgement

The authors gratefully acknowledge the support of the University of Strathclyde, the Royal Society (IE140842), the International Cooperation and Exchange Project NSFC (11511130057) and the National Science Foundation for Distinguished Young Scholars of China (11325211) during the course of this work.

Data availability

The raw data required to reproduce these findings are available to download from <http://dx.doi.org/10.15129/13787d1c-1741-4445-a042-b33e021ba8e5>.

References

Abaqus, C., 2013. Software for finite element analysis Abaqus/Complete Abaqus Environment, Version 6.12. Dassault Systèmes. Vélizy-Villacoublay.

Aboudi, J., Arnold, S.M., Bednarczyk, B.A., 2012. Micromechanics of composite materials: a generalized multiscale analysis approach. Butterworth-Heinemann.

- Barbera, D., Chen, H., Liu, Y., 2016a. Creep-fatigue behaviour of aluminum alloy-based metal matrix composite. *International Journal of Pressure Vessels and Piping* 139–140, 159-172.
- Barbera, D., Chen, H., Liu, Y., 2016b. On Creep Fatigue interaction of components at elevated temperature. *Journal of Pressure Vessel Technology* 138, 041403.
- Bettge, D., Günther, B., Wedell, W., Portella, P.D., Hemptenmacher, J., Peters, P., Skrotzki, B., 2007. Mechanical behavior and fatigue damage of a titanium matrix composite reinforced with continuous SiC fibers. *Materials Science and Engineering: A* 452, 536-544.
- Bree, J., 1967. Elastic-plastic behaviour of thin tubes subjected to internal pressure and intermittent high-heat fluxes with application to fast-nuclear-reactor fuel elements. *Journal of strain analysis* 2, 226-238.
- Cantor, B., Dunne, F.P., Stone, I.C., 2003. *Metal and ceramic matrix composites*. CRC Press.
- Chen, H., 2010. Lower and upper bound shakedown analysis of structures with temperature-dependent yield stress. *Journal of Pressure Vessel Technology* 132, 011202.
- Chen, H., Chen, W., Ure, J., 2014. A Direct Method on the Evaluation of Cyclic Steady State of Structures With Creep Effect. *Journal of Pressure Vessel Technology* 136, 061404-061404.
- Chen, H., Ponter, A.R., 2005. On the behaviour of a particulate metal matrix composite subjected to cyclic temperature and constant stress. *Computational materials science* 34, 425-441.
- Chen, H., Ponter, A.R., 2006. Linear Matching Method on the evaluation of plastic and creep behaviours for bodies subjected to cyclic thermal and mechanical loading. *International Journal for Numerical Methods in Engineering* 68, 13-32.
- Chen, H., Ponter, A.R., 2010. A direct method on the evaluation of ratchet limit. *Journal of Pressure Vessel Technology* 132, 041202.
- Chen, M., Hachemi, A., 2014. Progress in plastic design of composites, *Direct Methods for Limit States in Structures and Materials*. Springer, pp. 119-138.
- Coffin Jr, L., 1954. A study on the effects of cyclic thermal stress on a ductile metal. *Trans. ASME* 76.
- EDF Energy, 2014. Assessment procedure for the high temperature response of structures, R5 Issue 3, .
- Giugliano, D., Barbera, D., Chen, H., 2017. Effect of fiber cross section geometry on cyclic plastic behavior of continuous fiber reinforced aluminum matrix composites. *European Journal of Mechanics-A/Solids* 61, 35-46.
- Giugliano, D., Chen, H., 2016. Micromechanical modeling on cyclic plastic behavior of unidirectional fiber reinforced aluminum matrix composites. *European Journal of Mechanics - A/Solids* 59, 155-164.
- Gorash, Y., Chen, H., 2013. Creep-fatigue life assessment of cruciform weldments using the linear matching method. *International Journal of Pressure Vessels and Piping* 104, 1-13.
- Hales, R., 1980. A QUANTITATIVE METALLOGRAPHIC ASSESSMENT OF STRUCTURAL DEGRADATION OF TYPE 316 STAINLESS STEEL DURING CREEP-FATIGUE. *Fatigue & Fracture of Engineering Materials & Structures* 3, 339-356.
- Hales, R., Holdsworth, S., O'Donnell, M., Perrin, I., Skelton, R., 2002. A code of practice for the determination of cyclic stress-strain data. *Materials at high temperatures* 19, 165-185.
- Halford, G.R., Lerch, B.A., Arya, V.K., 2000. Thermal strain fatigue modeling of a matrix alloy for a metal matrix composite, *Thermo-mechanical Fatigue Behavior of Materials: Third Volume*. ASTM International.

- Hertz-Clemens, S., Aumont, C., Rémy, L., 2002. Damage mechanisms under thermal-Mechanical fatigue in a unidirectionally reinforced SiC-titanium metal matrix composite for advanced jet engine components. *European Structural Integrity Society* 29, 125-133.
- Jansson, S., Dal Bello, D., Leckie, F., 1994. Transverse and cyclic thermal loading of the fiber reinforced metal-matrix composite SCS6/Ti-15-3. *Acta metallurgica et materialia* 42, 4015-4024.
- Jansson, S., Leckie, F., 1992. Mechanical behavior of a continuous fiber-reinforced aluminum matrix composite subjected to transverse and thermal loading. *Journal of the Mechanics and Physics of Solids* 40, 593-612.
- Karakaş, Ö., Szusta, J., 2015. Monotonic and low cycle fatigue behaviour of 2024-T3 aluminium alloy between room temperature and 300 °C for designing VAWT components. *Fatigue & Fracture of Engineering Materials & Structures*.
- Manson, S., 1965. Fatigue: a complex subject—some simple approximations. *Experimental mechanics* 5, 193-226.
- Manson, S., Halford, G., 1976. Treatment of multiaxial creep-fatigue by strainrange partitioning.
- Manson, S.S., 1954. Behavior of materials under conditions of thermal stress. NACA.
- Manson, S.S., 1968. A simple procedure for estimating high-temperature low-cycle fatigue. *Experimental Mechanics* 8, 349-355.
- Maximov, J., Duncheva, G., Anchev, A., Ichkova, M., 2014. Modeling of strain hardening and creep behaviour of 2024T3 aluminium alloy at room and high temperatures. *Computational Materials Science* 83, 381-393.
- Mirdamadi, M., Johnson, W.S., 1996. Modeling and life prediction methodology for titanium matrix composites subjected to mission profiles, *Life Prediction Methodology for Titanium Matrix Composites*. ASTM International.
- Mondali, M., Abedian, A., Adibnazari, S., 2005. FEM study of the second stage creep behavior of Al6061/SiC metal matrix composite. *Computational Materials Science* 34, 140-150.
- Muralidharan, U., Manson, S., 1988. A modified universal slopes equation for estimation of fatigue characteristics of metals. *Journal of Engineering Materials and Technology* 110, 55-58.
- Nicholas, T., Russ, S.M., Neu, R.W., Schehl, N., 1996. Life prediction of a [0/90] metal matrix composite under isothermal and thermomechanical fatigue, *Life Prediction Methodology for Titanium Matrix Composites*. ASTM International.
- Plumbridge, W., 1987. Metallography of high temperature fatigue. *High Temperature Fatigue*, Springer, Dordrecht, 177-228.
- Ponter, A., Leckie, F., 1998a. Bounding properties of metal-matrix composites subjected to cyclic thermal loading. *Journal of the Mechanics and Physics of Solids* 46, 697-717.
- Ponter, A., Leckie, F., 1998b. On the behaviour of metal matrix composites subjected to cyclic thermal loading. *Journal of the Mechanics and Physics of Solids* 46, 2183-2199.
- Rutecka, A., Kowalewski, Z.L., Pietrzak, K., Dietrich, L., Makowska, K., Woźniak, J., Kostecki, M., Bochniak, W., Olszyna, A., 2011. Damage development of Al/SiC metal matrix composite under fatigue, creep and monotonic loading conditions. *Procedia Engineering* 10, 1420-1425.
- Skelton, R., Maier, H., Christ, H.-J., 1997. The Bauschinger effect, Masing model and the Ramberg–Osgood relation for cyclic deformation in metals. *Materials Science and Engineering: A* 238, 377-390.
- Wada, Y., Aoto, K., Ueno, F., 1997. Creep-fatigue evaluation method for type 304 and 316FR SS.

Xuanchen Zhu, H.C., Fuzhen Xuan, Xiaohui Chen., 2017. Cyclic plasticity behaviors of steam turbine rotor subjected to cyclic thermal and mechanical loads., European Journal of Mechanics - A/Solids, Volume 66, 243-255.

ACCEPTED MANUSCRIPT

Highlights

- A modification of the existing strain-range partitioning procedure for dealing with creep-fatigue interaction of composites have been proposed
- When the off-axis mechanical load dominates over the thermal load, creep ratchetting is observed for all the geometries investigated
- For the geometries and load conditions examined, the high temperature creep damage dominates over the fatigue damage
- Both fibre cross section geometry and fibre arrangement can be detrimental regarding the creep-fatigue life by enhancing the geometrical constraint